

## Glass Transitions in Complex Bituminous Binders [PPT]

Apostolidis, P.; Porot, Laurent; Elwardany, Michael; Vansteenkiste, Stefan; Chailleux, Emmanuel

**Publication date**

2022

**Document Version**

Final published version

**Citation (APA)**

Apostolidis, P., Porot, L., Elwardany, M., Vansteenkiste, S., & Chailleux, E. (2022). *Glass Transitions in Complex Bituminous Binders [PPT]*. Abstract from 57th Petersen Asphalt Research Conference.

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

## **RILEM TC 272 PIM TG1 : Glass Transitions in Complex Bituminous Binders**

Panos Apostolidis <sup>a</sup>, Laurent Porot <sup>b</sup>, Michael Elwardany <sup>c</sup>, Stefan Vansteenkiste <sup>d</sup> & Emmanuel Chailleux <sup>e</sup>

<sup>a</sup> Delft University of Technology, Delft, the Netherlands  
[p.apostolidis@tudelft.nl](mailto:p.apostolidis@tudelft.nl)

<sup>b</sup> Kraton Polymers B.V., the Netherlands  
[laurent.porot@kraton.com](mailto:laurent.porot@kraton.com)

<sup>c</sup> Western Research Institute, Laramie, USA  
[michael.elwardany@uwyo.edu](mailto:michael.elwardany@uwyo.edu)

<sup>d</sup> Belgian Road Research Centre (BRRC), Brussels, Belgium  
[s.vansteenkiste@brrc.be](mailto:s.vansteenkiste@brrc.be)

<sup>e</sup> Université Gustave Eiffel, Bougenas, France  
[emmanuel.chailleux@univ-eiffel.fr](mailto:emmanuel.chailleux@univ-eiffel.fr)

The RILEM TC 272 PIM (Phase and Interphase behaviour of innovative bituminous Materials) – TG1 Binder has initiated an inter-laboratory program investigating the phase and interphase behaviour of bituminous binders. Five laboratories evaluated the low temperature properties of seven standard and complex binders with differential scanning calorimetry (DSC). DSC has been accepted as a powerful tool to evaluate, among others, the glass transitions,  $T_g$ , monitoring the endothermic or exothermic heat flow of a material under controlled temperature conditions. There are different ways to run the test, conventional temperature linear-DSC (TL-DSC), and temperature modulation-DSC (TM-DSC). The latter has been proven as an efficient method differentiating the structural relaxation phenomena from the heat capacity. In this study, emphasis was laid on comparing the  $T_g$  measured by TL- and TM-DSC improving the interpretation of binder glass transitions. To restrain the scope of this study, two SBS polymer modified binders (PmBs), a commercially available PmB and an highly modified PmB (7.5 % SBS) , were evaluated and compared with two neat bituminous binders. It was observed that the modification by 7.5% SBS resulted in a decrease of the  $T_g$ . This reduction of  $T_g$  reflects the positive influence of SBS at low temperatures.



**RILEM TC 272 PIM TG1**

**Glass Transitions in Complex Bituminous Binders**

*In 2020 Petersen Asphalt Research Conference*

P. Apostolidis<sup>1</sup>, L. Porot<sup>2</sup>, M. Elwardany<sup>3</sup>,  
S. Vansteenkiste<sup>4</sup> & E. Chailleux<sup>5</sup>

<sup>1</sup> TU Delft, <sup>2</sup> Kraton Polymers, <sup>3</sup> WRI, <sup>4</sup> BRRC,

<sup>5</sup> Université Gustave Eiffel

# The RILEM PIM



## Rilem TC 272 - **P**hase and **I**nterphase in bituminous **M**aterials


- TG1 is about testing of complex bituminous binders
  - 17 labs participating from Europe and US
- Experiments
  - Physical properties and chemical structure
  - In a wide range of conditions

	Label	Description
Group 1	<b>Bit1</b>	Straight run bitumen 35/50 source Europe
	<b>PmB1</b>	Commercial Polymer modified Bitumen as for TG2
	<b>PmB2</b>	Lab made highly modified bitumen with 7.5 % SBS (HiMA)
Group 2	<b>Bit2</b>	Straight run bitumen 70/100 source Europe
	<i>Blend1</i>	<i>Bit1 + asphalt reuse additive as for TC RAP TG3</i>
	<i>Blend2</i>	<i>Bit1 + REOB</i>
	<i>Blend3</i>	<i>Bit1 + paraffinic oil</i>

# Glass transition in binders



- Binders behave as glassy materials below the glass transition temperature ( $T_g$ ), while above the  $T_g$  they behave as amorphous.
- The glass transition region is the temperature range that corresponds to the glass-to-amorphous transition. For binders, this region is between -50 and 0°C.
- The glass transition can assist on understanding the thermal cracking of binders.

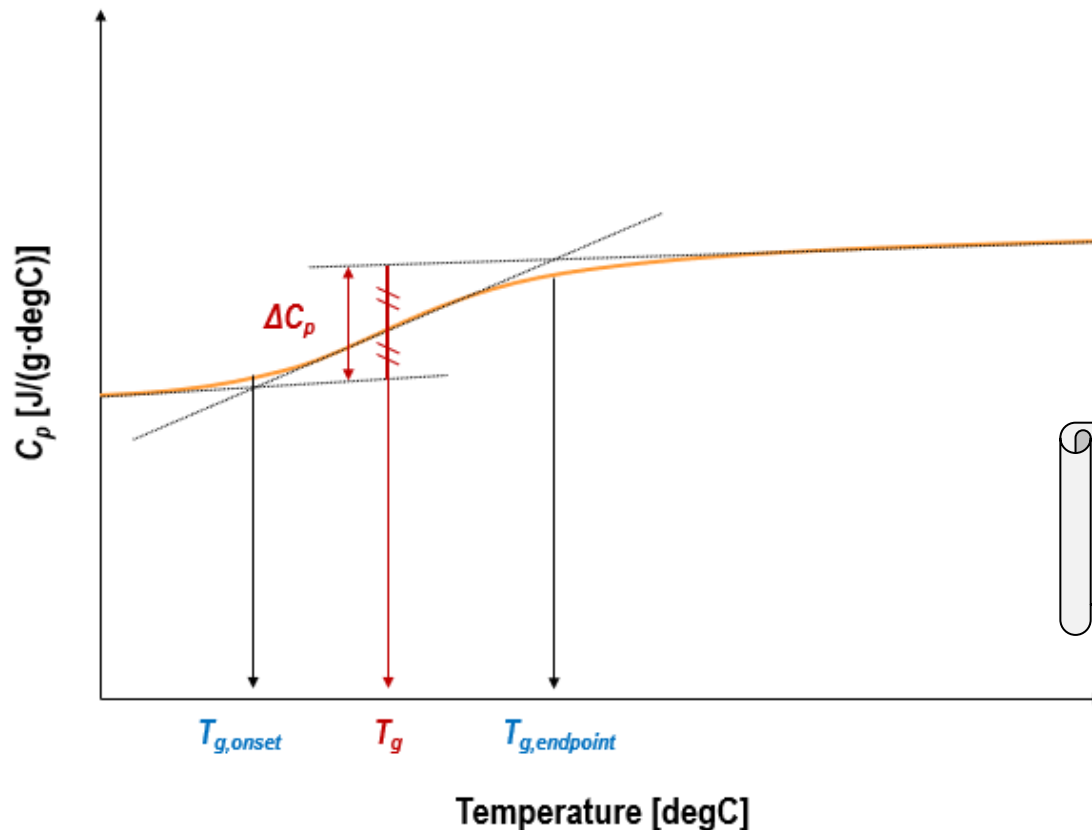

$T_g$  : the half-height between the heat capacity ( $C_p$ ) of  $T_{g,onset}$  &  $T_{g,endpoint}$

# Differential scanning calorimetry (DSC)



DSC measures the differences in heat flow [mW=mJ/sec] into a substance and a reference as a function of time and temperature, under a controlled temperature program.

$$\frac{dH}{dt} = \text{DSC heat flow signal}$$

$$C_p = \text{Sample Heat Capacity} \\ = \text{Sample Specific Heat} \times \text{Sample Weight}$$

$$\frac{dH}{dt} = C_p \frac{dT}{dt} + f(T, t)$$

$$\frac{dT}{dt} = \text{Heating Rate}$$

$$f(T, t) = \text{Heat flow that is function of time} \\ \text{at an absolute temperature (kinetic)}$$

# Differential scanning calorimetry (DSC)



DSC measures the differences in heat flow (mW=mJ/sec) into a substance and a reference as a function of time and temperature, under a controlled temperature program.

- When measuring the  $T_g$ , the molecular motion associated with the glass transitions is time dependent. The  $T_g$  increases when heating rate increases in DSC
- When reporting the  $T_g$ , it is necessary to state the experimental conditions (heating rate, sample size, etc.) and how the  $T_g$  is determined

# Different laboratories



## Lab1 TL-DSC:protocol1

1	Isothermal   165 degC	for 5 min
2	Non-isothermal   2 degC/min	to -60 degC
3	Isothermal   -60 degC	for 5 min
4	Non-isothermal   2 degC/min	to 165 degC

### DSC Q2000, TA

## Lab2 TM-DSC:protocol1

1	Isothermal   165 degC	for 5 min
2	Non-isothermal   5 degC/min	to -90 degC
3	Isothermal   -90 degC	for 5 min
4	Modulation   10 degC/min	0.5 degC for 80 sec to 165 degC
5	Isothermal   165 degC	for 5 min
6	Non-isothermal   2 degC/min	to -90 degC
7	Isothermal   -90 degC	for 5 min
8	Non-isothermal   2 degC/min	to 165 degC

### DSC Q2000, TA

## Lab5 TM-DSC:protocol2


1	Isothermal   165 degC	for 5 min
2	Modulation   2 degC/min	0.5 degC for 60 sec to -60 degC
3	Isothermal   -60 degC	for 5 min
4	Modulation   2 degC/min	0.5 degC for 60 sec to -60 degC

### DSC 6000, PerkinElmer

## Lab12 TL-DSC:protocol2

1	Isothermal   25 degC	
2	Non-isothermal   20 degC/min	to 130 degC
3	Isothermal   130 degC	for 1 min
4	Non-isothermal   10 degC/min	to -80 degC
5	Isothermal   -80 degC	for 1 min
6	Non-isothermal   10 degC/min	to 160 degC
7	Isothermal   160 degC	for 1 min
8	Non-isothermal   10 degC/min	to -80 degC
9	Isothermal   -80 degC	for 1 min
10	Non-isothermal   10 degC/min	to 0 degC
11	Isothermal   0 degC	for 5 min
12	Non-isothermal   10 degC/min	to -80 degC
13	Isothermal   -80 degC	for 1 min
14	Non-isothermal   20 degC/min	to 160 degC

### DSC2 STARe with M-DSC TOPEM, Mettler Toledo

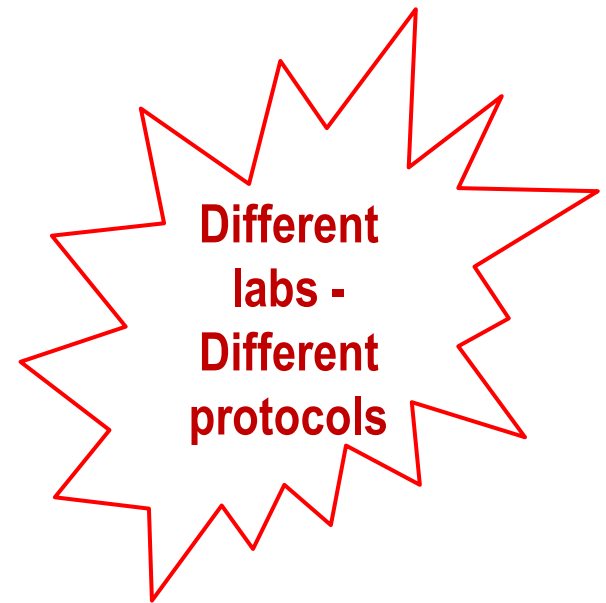

Temperature-Linear (TL-DSC)

Temperature-Modulation (TM-DSC)



# Binders

---



To restrain the scope of this study, 4 binders were evaluated :

**Bit1** – 35/50 penetration graded bituminous binder [PG 70-22]



**Bit2** – 70/100 penetration graded bituminous binder [PG 64-22]

**PmB1** – Commercial polymer modified binder (plant-produced) [PG 76-16]

**PmB2** – Bit2 modified with 7,5% of SBS (lab-produced) [HiMA, PG 88-28]



# TL-DSC: Heat flow & derivatives

(Bit1 & Bit2, by Lab1)

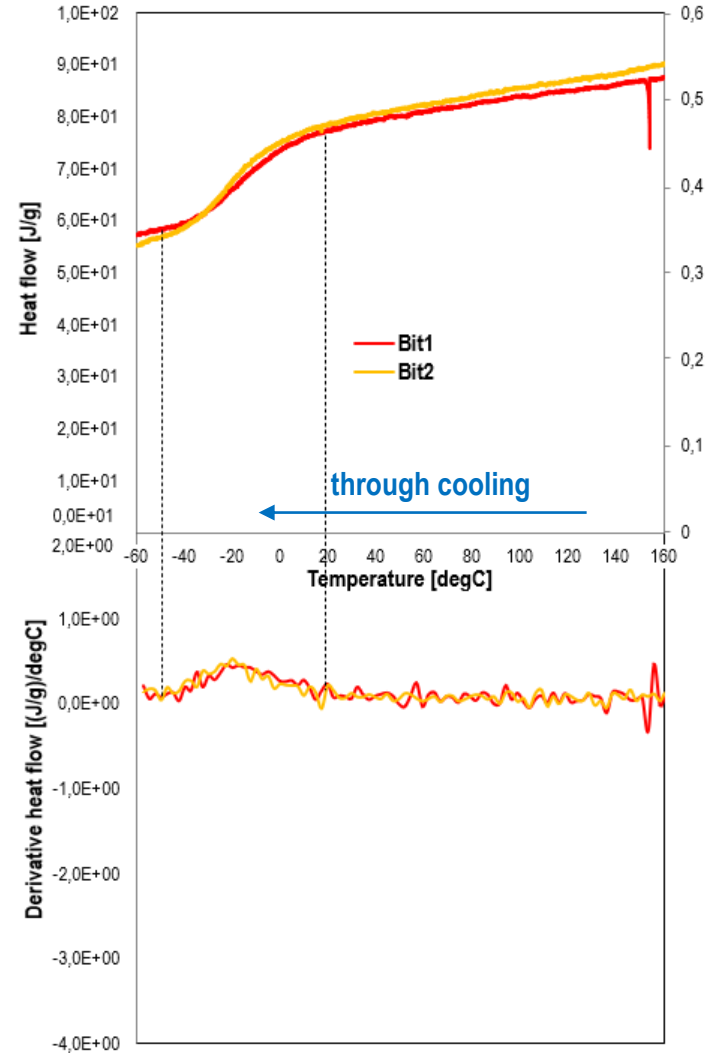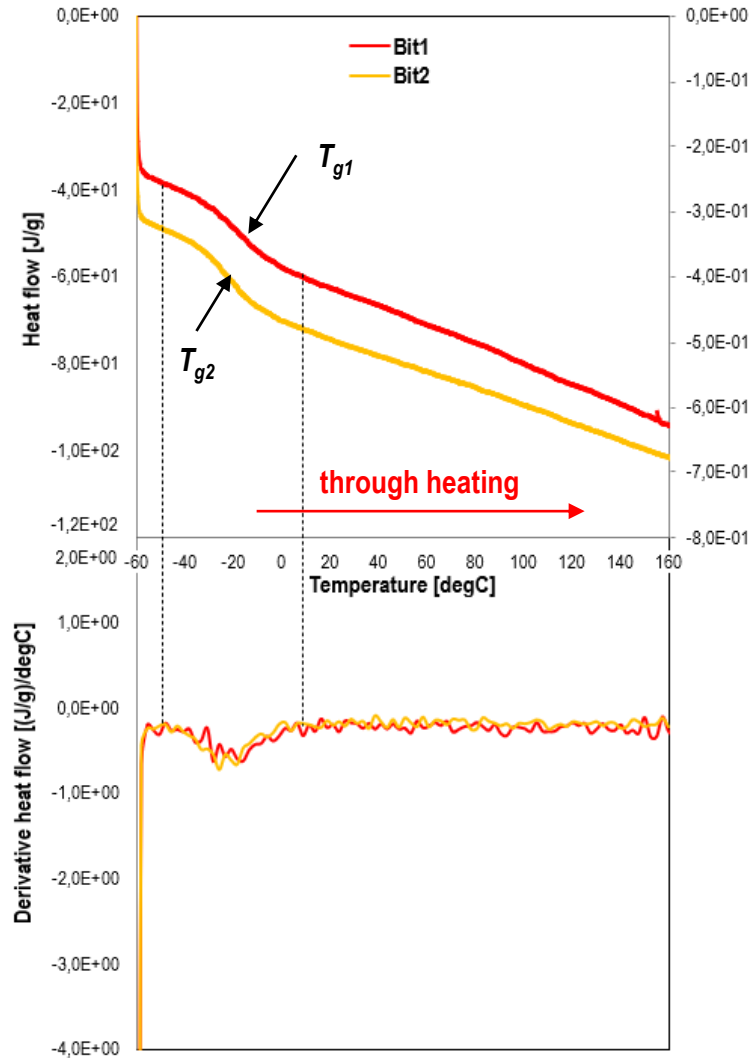

# TL-DSC: Heat flow & derivatives


(PmB1 & PmB2, by Lab1)

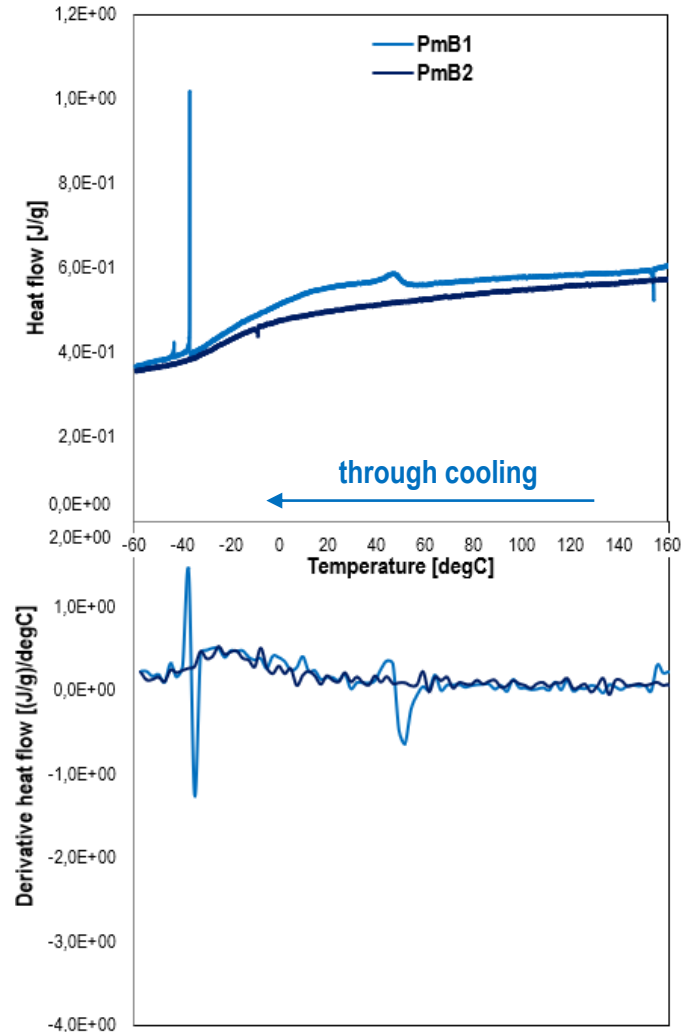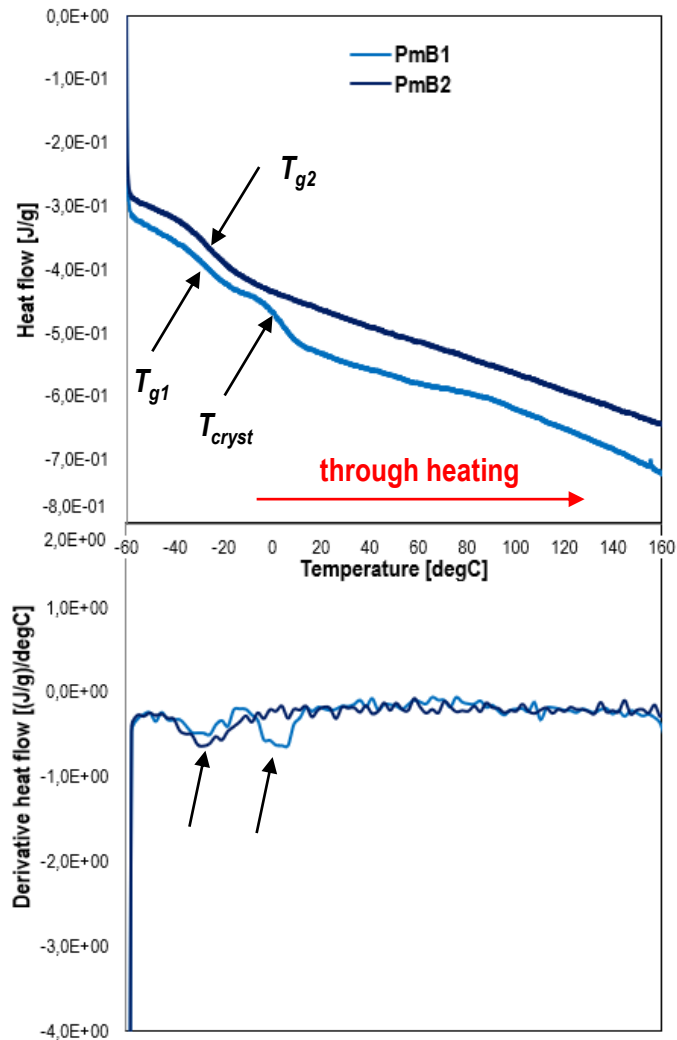


\* **Cold crystallization** – the exothermic transition during heating from a solid amorphous to a solid crystalline state.

# TL-DSC: With different protocols

(PmB1 & PmB2, through heating)

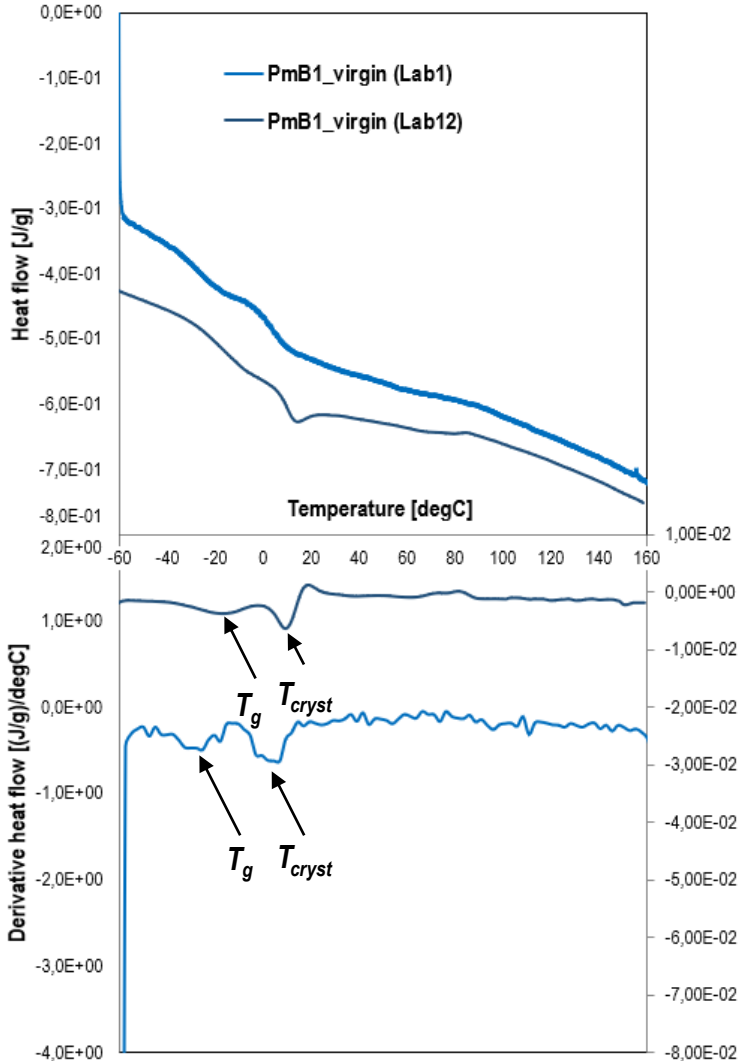



PmB1

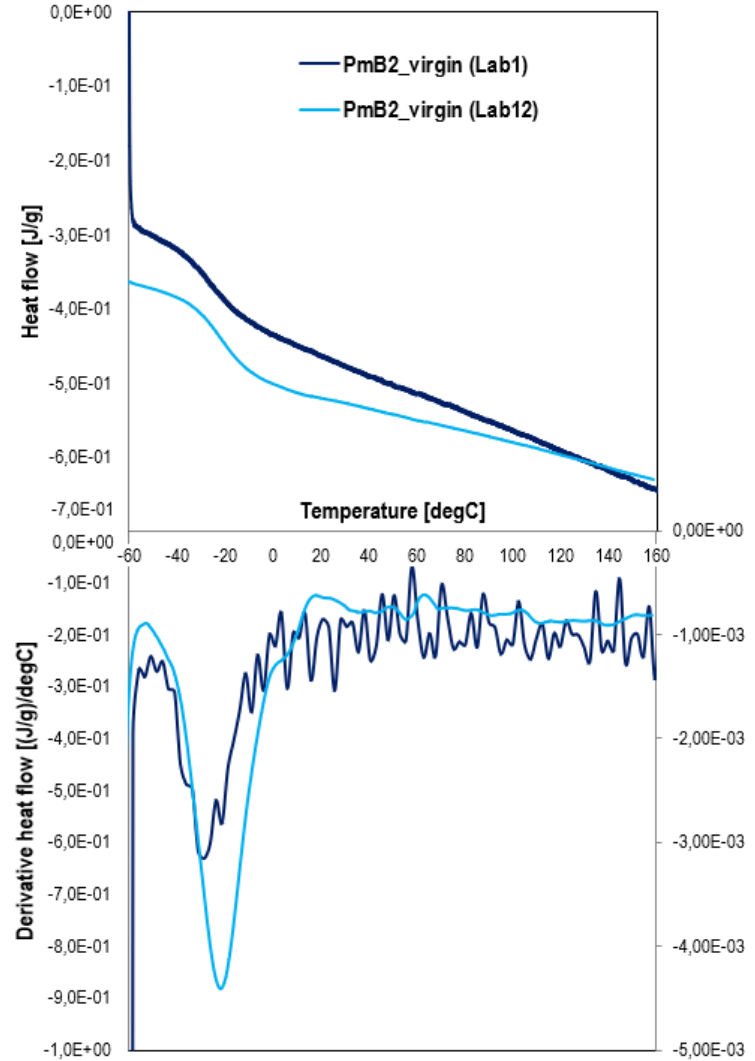

PmB2

# TM-DSC: Heat capacity & derivatives



(PmB1 & PmB2, through heating)

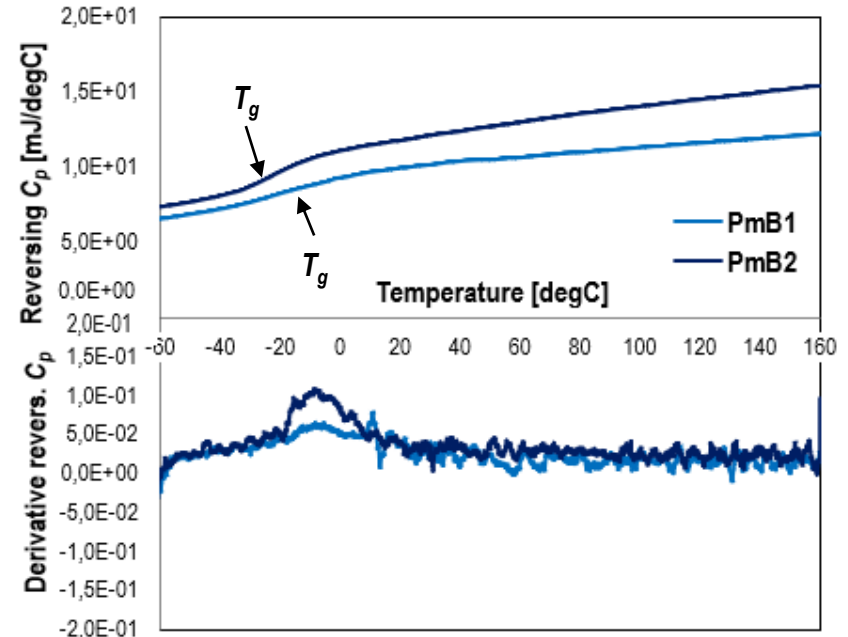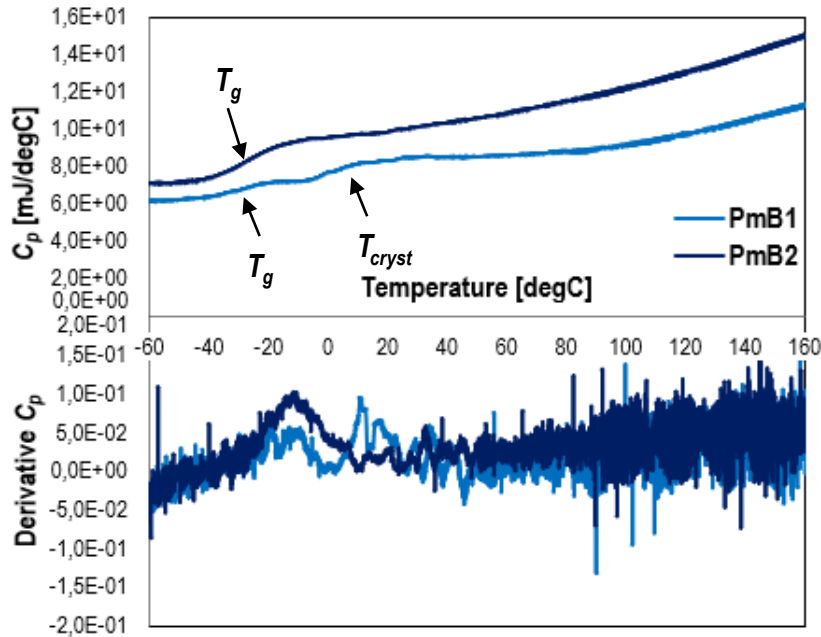

- No cold crystallization in reversing  $C_p$  curves.
- The  $T_g$  values of binders based on reversing  $C_p$  were higher than of total  $C_p$  curves.

# Impact of SBS

## (Bit2, PmB2 & SBS)

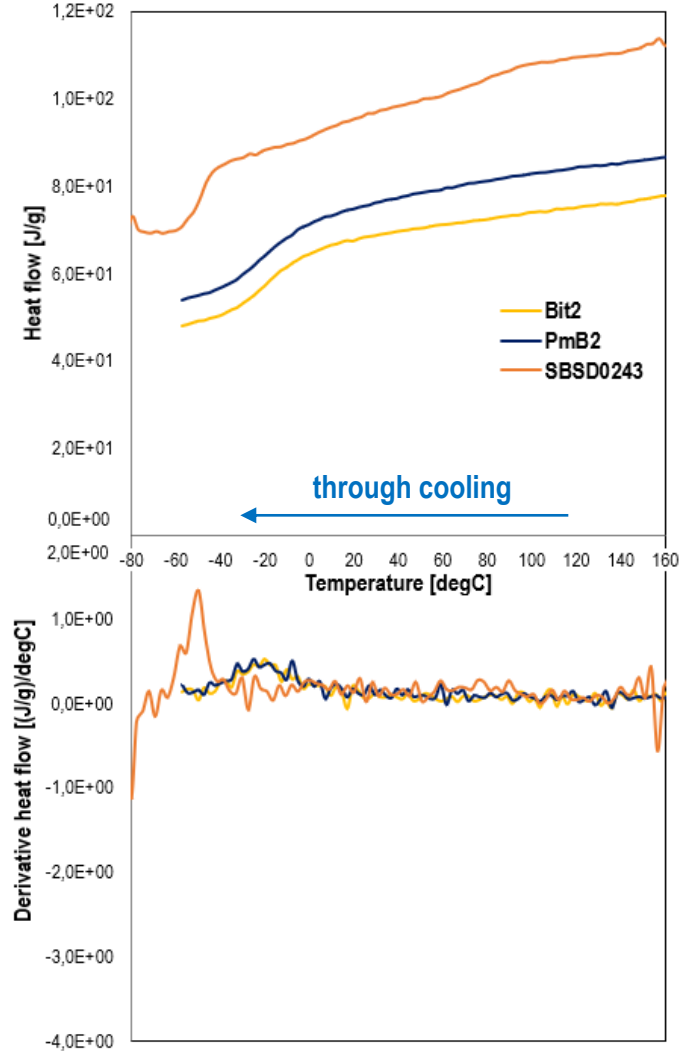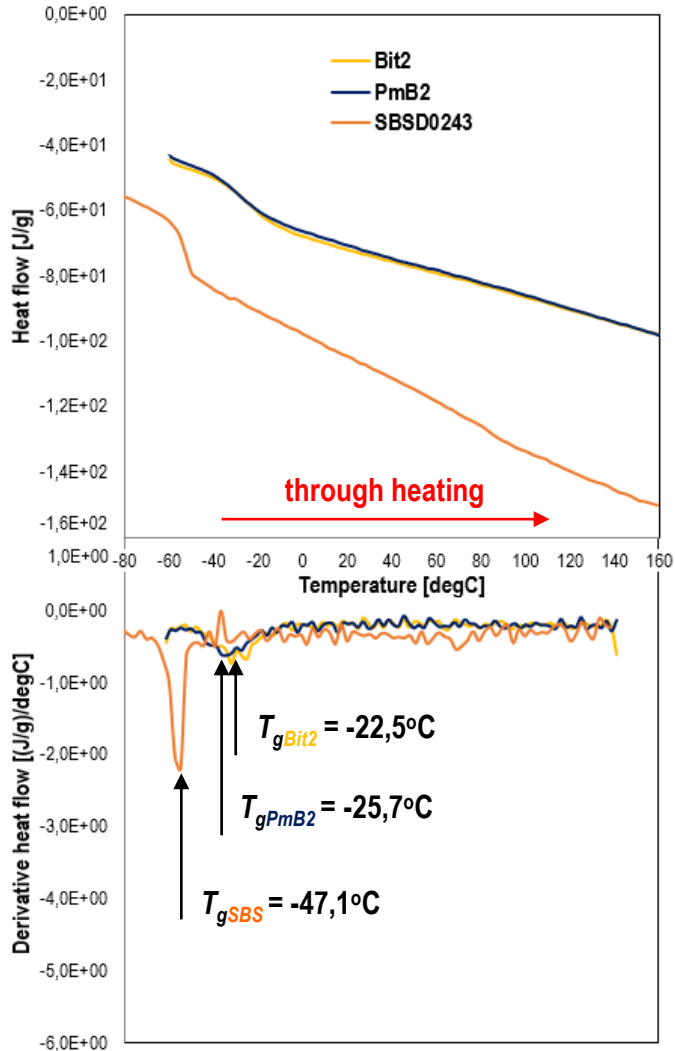

\* **SBSDO243** - Styrene-butadiene-styrene by KRA | polybutadiene blocks: sharp  $T_g$  at  $\approx -50^{\circ}\text{degC}$  | polystyrene blocks: broad  $T_g$  from 50 to 130degC

# Interlaboratory results



$T_g$  values determined based on the 1<sup>st</sup> derivative of heat flow (TL-DSC) and heat capacity (TM-DSC) through heating measurements

Sample	Glass transition temperature, $T_g$ [°C]			
	Lab1 <sup>*1</sup>	Lab2 <sup>*2</sup>	Lab5 <sup>*3</sup>	Lab12 <sup>*4</sup>
<b>Bit1</b>	-13,3	-10,5	-16,6	-14,5
<b>Bit2</b>	-22,5	-14,4	-23,3	-18,3
<b>PmB1</b>	-23,2	-16,9	-25,1	-16,8
<b>PmB2</b>	-25,7	-19,2	-25,0	-22,0

<sup>\*1</sup> TL-DSC: protocol1, <sup>\*2</sup> TM-DSC: protocol1, <sup>\*3</sup> TM-DSC: protocol2, <sup>\*4</sup> TL-DSC: protocol2

# Summary of findings so far



- The  $T_g$  values were determined by calculating the maximum of the 1<sup>st</sup> derivative of heat flow and  $C_p$  curves during heating.
- In heating TL-DSC,
  - ❑ a small reduction in the base-line of heat flow indicates the glass transition in binders,
  - ❑ the appearance of a second peak of 1<sup>st</sup> derivative is a result of cold crystallization. Cold crystallization after the glass transition in PmB1.
- In heating TM-DSC,
  - ❑ PmB1 did not show two peaks of 1<sup>st</sup> derivative of reversing  $C_p$ ,
  - ❑ thus, the TM-DSC allowed the separation of structural relaxation phenomena from the total  $C_p$  measurements.
- The polymer modification resulted in the  $T_g$  reduction.

Link of DSC with BBR and DSR 4-mm results | Aging studies





**RILEM TC 272 PIM TG1**

**Glass Transitions in Complex Bituminous Binders**

*In 2020 Petersen Asphalt Research Conference*



Thank you !