

**VUV-UV-vis photoluminescence, X-ray radioluminescence and energy transfer dynamics of Ce<sup>3+</sup> and Eu<sup>2+</sup> in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>**

Wen, Donghao; Li, Quanfeng; Ou, Yiyi; Yang, Yunlin; Qi, Zeming; Dorenbos, Pieter; Liang, Hongbin

**DOI**

[10.1039/d2dt03165e](https://doi.org/10.1039/d2dt03165e)

**Publication date**

2022

**Document Version**

Final published version

**Published in**

Dalton Transactions

**Citation (APA)**

Wen, D., Li, Q., Ou, Y., Yang, Y., Qi, Z., Dorenbos, P., & Liang, H. (2022). VUV-UV-vis photoluminescence, X-ray radioluminescence and energy transfer dynamics of Ce<sup>3+</sup> and Eu<sup>2+</sup> in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>. *Dalton Transactions*, 51(46), 17809-17819. <https://doi.org/10.1039/d2dt03165e>

**Important note**

To cite this publication, please use the final published version (if applicable). Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

***Green Open Access added to TU Delft Institutional Repository***

***'You share, we take care!' - Taverne project***

**<https://www.openaccess.nl/en/you-share-we-take-care>**

Otherwise as indicated in the copyright section: the publisher is the copyright holder of this work and the author uses the Dutch legislation to make this work public.

Cite this: *Dalton Trans.*, 2022, **51**, 17809

# VUV-UV-vis photoluminescence, X-ray radioluminescence and energy transfer dynamics of Ce<sup>3+</sup> and Eu<sup>2+</sup> in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>†

Donghao Wen,<sup>a</sup> Quanfeng Li,<sup>a</sup> Yiyi Ou,<sup>a</sup> Yunlin Yang,<sup>a</sup> Zeming Qi,<sup>b</sup> Pieter Dorenbos<sup>c</sup> and Hongbin Liang<sup>\*a</sup>

Ce<sup>3+</sup> and Eu<sup>2+</sup> doped and Ce<sup>3+</sup>–Eu<sup>2+</sup> co-doped Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> phosphors are prepared via a high-temperature solid-state reaction technique. The synchrotron radiation vacuum ultraviolet-ultraviolet (VUV-UV) excitation and ultraviolet-visible (UV-vis) emission spectra of diluted Ce<sup>3+</sup> and Eu<sup>2+</sup> doped Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> samples are measured at cryogenic temperatures. The electron-vibrational interaction (EVI) between Ce<sup>3+</sup> and its surroundings is analyzed. The dependencies of the 4f–5d transitions of Ce<sup>3+</sup> on the structure of the host compounds Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>, Ba<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> and BaMg<sub>2</sub>Si<sub>2</sub>O<sub>7</sub> are discussed in detail. Then the thermal quenching channel is proposed based on the measurements of temperature dependent luminescence intensities and decay times of Ce<sup>3+</sup> and Eu<sup>2+</sup> in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>, and the Ce<sup>3+</sup> → Eu<sup>2+</sup> energy transfer mechanism is understood by three luminescence dynamic models. In addition, Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>:Ce<sup>3+</sup>/Eu<sup>2+</sup> samples are evaluated for the possibilities of X-ray detection applications using X-ray excited luminescence (XEL) spectroscopy, and it was found that they are not suitable.

Received 29th September 2022,

Accepted 28th October 2022

DOI: 10.1039/d2dt03165e

rsc.li/dalton

## 1. Introduction

Luminescence of Ce<sup>3+</sup> and Eu<sup>2+</sup> plays an important role in the detection of ionizing radiation due to their parity-allowed 4f–5d transitions. Numerous inorganic compounds doped with Ce<sup>3+</sup> or Eu<sup>2+</sup> ions have been widely studied, and materials such as Lu<sub>2</sub>SiO<sub>5</sub>:Ce<sup>3+</sup> and SrI<sub>2</sub>:Eu<sup>2+</sup> with outstanding luminescence properties are commercially available scintillators.<sup>1</sup> In addition, materials like Y<sub>3</sub>Al<sub>5</sub>O<sub>12</sub>:Ce<sup>3+</sup> and BaMgAl<sub>10</sub>O<sub>17</sub>:Eu<sup>2+</sup> serve successfully as yellow and blue emitting phosphors in light-emitting diodes (LEDs) and tricolor tubes for lighting and displays, respectively.<sup>2</sup> To find novel luminescent materials and to improve their luminescence performances, much attention has been directed toward energy transfer (ET) from and to Ce<sup>3+</sup> and Eu<sup>2+</sup> ions.<sup>3,4</sup>

The composition and structure of a host compound are essential for the luminescence property of a phosphor, because it directly rules the 4f–5d transitions of Ce<sup>3+</sup> and/or Eu<sup>2+</sup> in this compound. Silicates are suitable as host compounds for the

luminescence of lanthanide and transition metal ions.<sup>5,6</sup> Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> with akermanite structure is of particular interest to us in these silicates.<sup>7–10</sup> A similar composition of Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> to those of Ba<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> and BaMg<sub>2</sub>Si<sub>2</sub>O<sub>7</sub>, and the single Sr<sup>2+</sup>/Ba<sup>2+</sup> site in these compounds make Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> an appropriate choice for studying the composition and structure dependent 4f–5d transitions and energy transfer of Ce<sup>3+</sup> and Eu<sup>2+</sup> ions.

In this paper, synchrotron radiation VUV-UV excitation and UV-vis emission spectra are recorded to fully understand the 5d energies of Ce<sup>3+</sup> in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>, and the electron–phonon coupling of Ce<sup>3+</sup> is analyzed in consideration of its significant influences on luminescence performances such as the Stokes shift and the bandwidth. In particular, the impacts of coordination surroundings on the 5d energies and luminescence properties of Ce<sup>3+</sup> ions are systematically discussed for three compounds Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub>, Ba<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> and BaMg<sub>2</sub>Si<sub>2</sub>O<sub>7</sub> with similar compositions. Furthermore, the thermal quenching channel of Ce<sup>3+</sup> and Eu<sup>2+</sup> ions, and the Ce<sup>3+</sup>–Eu<sup>2+</sup> energy transfer dynamics in Sr<sub>2</sub>MgSi<sub>2</sub>O<sub>7</sub> are discussed in detail. Finally, XEL measurements are performed to assess the application possibilities of Ce<sup>3+</sup> and Eu<sup>2+</sup> doped phosphors for X-ray detection.

## 2. Experimental

### 2.1 Sample preparation

Three series of powder samples, Sr<sub>2–2x</sub>Ce<sub>x</sub>Na<sub>x</sub>MgSi<sub>2</sub>O<sub>7</sub> (x = 0, 0.001, 0.005, 0.03), Sr<sub>2–x</sub>Eu<sub>x</sub>MgSi<sub>2</sub>O<sub>7</sub> (x = 0.001, 0.003) and

<sup>a</sup>MOE Key Laboratory of Bioinorganic and Synthetic Chemistry, KLGHEI of Environment and Energy Chemistry, School of Chemistry, Sun Yat-sen University, Guangzhou 510006, China

<sup>b</sup>National Synchrotron Radiation Laboratory, University of Science and Technology of China, Hefei 230029, China

<sup>c</sup>Faculty of Applied Sciences, Delft University of Technology, 2629 JB Delft, The Netherlands

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2dt03165e>

$\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_x\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  ( $x = 0.001, 0.005, 0.01$ ), were prepared *via* a high-temperature solid-state reaction technique.  $\text{SrCO}_3$  (Analytical Reagent, A.R.),  $4\text{MgCO}_3 \cdot \text{Mg}(\text{OH})_2 \cdot 5\text{H}_2\text{O}$  (A.R.),  $\text{SiO}_2$  (99.99%),  $\text{CeO}_2$  (99.99%), and  $\text{Eu}_2\text{O}_3$  (99.99%) were used as the initial materials. 4 mol%  $\text{H}_3\text{BO}_3$  (A.R.) was added as a flux, and the aliovalent substitution between trivalent  $\text{Ce}^{3+}$  and divalent  $\text{Sr}^{2+}$  in samples  $\text{Sr}_{2-2x}\text{Ce}_x\text{Na}_x\text{MgSi}_2\text{O}_7$  and  $\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_x\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  was balanced by using monovalent  $\text{Na}^+$  provided by  $\text{Na}_2\text{CO}_3$  (99.99%) as charge compensators. The stoichiometric raw materials were ground in an agate mortar and then calcined at 1523 K for 4 h in a CO reducing ambience. The target products were obtained by grinding after cooling down to room temperature (RT).

## 2.2 Measurements

The phase purity of the samples was checked *via* the powder X-ray diffraction (XRD) technique using a Rigaku D-MAX 2200 VPC X-ray diffractometer with Cu  $K\alpha$  radiation ( $\lambda = 1.5418 \text{ \AA}$ ) at 40 kV and 26 mA. The Rietveld structural refinement of the host compound was performed using the TOPAS-Academic program,<sup>11</sup> and then its high quality XRD data were collected using a Bruker D8 advanced X-ray diffractometer with Cu  $K\alpha$  radiation ( $\lambda = 1.5418 \text{ \AA}$ ) at 40 kV and 40 mA with a step interval of  $0.02^\circ$ . The far infrared reflectance spectrum of the host compound was recorded on the BL01B beamline of the National Synchrotron Radiation Laboratory (NSRL, Hefei, China) at RT.<sup>12</sup>

An Edinburgh FLS1000 combined fluorescence lifetime and steady state spectrometer was used to record UV-vis excitation/emission spectra and luminescence decay curves. A 450 W xenon lamp was used as the excitation source for recording steady state luminescence spectra, and the excitation source used for obtaining luminescence decay curves was a 150 W nF900 lamp with a pulse width of 1 ns and a pulse rate of 40 kHz, or a 340 nm EPLED (picosecond pulsed light emitting diode) with a typical pulse width of 790 ps and a typical average power of 2.0  $\mu\text{W}$  at 10 MHz, respectively. The temperature of the samples is controlled using a MercuryTC Model temperature controller.

Synchrotron radiation VUV-UV excitation and corresponding emission spectroscopy were performed on the beamline 4B8 of the Beijing Synchrotron Radiation Facility (BSRF). XEL spectra were recorded using a Philips PW2253/20 X-ray tube at the Delft University of Technology, the Netherlands. More details can be found in ref. 13.

## 3. Results and discussion

### 3.1 XRD and crystal structure

The Rietveld refinement of the high-quality XRD data of the un-doped host compound  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  is first performed (Fig. S1(a)†). The acquired refinement parameters of  $R_p$ ,  $R_{wp}$ , and  $R_{bragg}$  are 3.906%, 5.220%, and 2.710%, respectively, which prove the reliability of the result and purity of the sample.  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  has a tetragonal structure with the space group  $P4_21m$ . The lattice parameters are  $a = b = 8.011 \text{ \AA}$ ,  $c =$


$5.165 \text{ \AA}$ , and  $V = 331.4 \text{ \AA}^3$ . There is only one eight-fold coordinated  $\text{Sr}^{2+}$  site with  $C_1$  symmetry in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  and the average  $\text{Sr}^{2+}-\text{O}^{2-}$  bond length is  $2.669 \text{ \AA}$  (Fig. S1(b)†).<sup>7</sup> The distance between the two nearest neighboring  $\text{Sr}^{2+}$  ions is  $3.743 \text{ \AA}$ . The  $\text{Mg}^{2+}$  and  $\text{Si}^{4+}$  ions connect to four oxygen ions to form regular tetrahedra. Fig. S1(c)† depicts the crystal structure of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ , which is a layer structure arrangement in the  $c$ -axis direction. The  $\text{Sr}^{2+}$  ions form a layer separately, while the  $\text{Mg}^{2+}$  and  $\text{Si}^{4+}$  tetrahedra form another layer together between  $\text{Sr}^{2+}$  ions. Two  $[\text{SiO}_4]^{2-}$  tetrahedra connect with each other *via* a corner-sharing oxygen ion and form a  $[\text{Si}_2\text{O}_7]^{6-}$  cluster.

The XRD patterns of typical  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ ,  $\text{Sr}_{2-2x}\text{Ce}_x\text{Na}_x\text{MgSi}_2\text{O}_7$  ( $x = 0.001, 0.03$ ),  $\text{Sr}_{2-x}\text{Eu}_x\text{MgSi}_2\text{O}_7$  ( $x = 0.001$ ) and  $\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_x\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  ( $x = 0.01$ ) samples at RT shown in Fig. S1(d)† match well with the standard card (PDF# 75-1736) of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ ,<sup>7</sup> showing that the impurity phase content would be below the detection limit of XRD if it existed in the samples and demonstrating that  $\text{Ce}^{3+}$ ,  $\text{Eu}^{2+}$  and  $\text{Na}^+$  ions do not significantly change the crystal structure. Due to the similar ion radii of eight-fold coordinated  $\text{Ce}^{3+}$  ( $\sim 1.14 \text{ \AA}$ ),  $\text{Na}^+$  ( $\sim 1.18 \text{ \AA}$ ),  $\text{Eu}^{2+}$  ( $\sim 1.25 \text{ \AA}$ ) and  $\text{Sr}^{2+}$  ( $\sim 1.26 \text{ \AA}$ ), the doped  $\text{Ce}^{3+}$ ,  $\text{Eu}^{2+}$  and  $\text{Na}^+$  ions are thought to occupy the  $\text{Sr}^{2+}$  sites in the samples.

### 3.2 Photoluminescence of $\text{Ce}^{3+}$ in $\text{Sr}_2\text{MgSi}_2\text{O}_7$

Fig. S2† shows the height-normalized excitation spectra at different emission wavelengths ( $\lambda_{em} = 350, 368, 373$  and  $382 \text{ nm}$ ) and the height-normalized emission spectra at varying excitation wavelengths ( $\lambda_{ex} = 267, 272, 277, 319, 326$  and  $332 \text{ nm}$ ) of the sample  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  at RT for comparison. It can be seen that either four normalized excitation curves or six normalized emission spectra well overlap each other, respectively. These phenomena indicate that the material does not contain impurities that affect the luminescence spectrum in this wavelength range, the doped  $\text{Ce}^{3+}$  ions occupy only one type of lattice site in the host compound and the inhomogeneous broadening of  $\text{Ce}^{3+}$  4f–5d transitions does not occur in this diluted sample.<sup>14</sup> As mentioned above, we deem that  $\text{Ce}^{3+}$  ions are incorporated into eight-fold coordinated  $\text{Sr}^{2+}$  sites. The excitation peaks at approximately 326 and 273 nm result from the first and the second 4f–5d excitation bands of  $\text{Ce}^{3+}$  in this  $[\text{SrO}_8]$  site of the host compound and their positions are in good agreement with those in Fig. 1 and close to those in references.<sup>9,15</sup> Two partially overlapped broad bands are seen in the emission curves and their peaks are at about 345 and 371 nm with an energy difference of about 0.24 eV ( $19.5 \times 10^3 \text{ cm}^{-1}$ ). Obviously, these two bands correspond to the transitions from the relaxed lowest (the first) 5d to  $^2F_J$  ( $J = 5/2, 7/2$ ) states of  $\text{Ce}^{3+}$  ions in the  $\text{Sr}^{2+}$  sites of the host compound.

Fig. 1 displays the VUV-UV excitation ( $\lambda_{em} = 370 \text{ nm}$ ) and corresponding emission ( $\lambda_{ex} = 270 \text{ nm}$ ) spectra of the sample  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  recorded by BSRF at 10 K. The typical broad doublet emission bands are at their maxima of about 345 and 368 nm in the emission spectrum, respectively. Their separation is clearer than that in Fig. S2† due to the

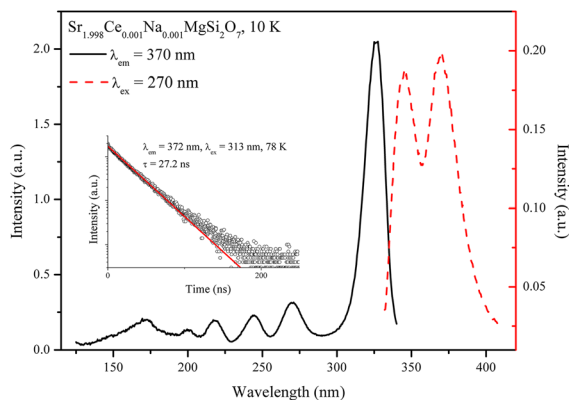

**Fig. 1** The synchrotron radiation VUV-UV excitation ( $\lambda_{em} = 370$  nm) and emission ( $\lambda_{ex} = 270$  nm) spectra of the sample  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  at 10 K. The inset shows its luminescence decay curve ( $\lambda_{ex} = 313$  nm,  $\lambda_{em} = 372$  nm) at 78 K.

measurement at a cryogenic temperature of 10 K in Fig. 1, and their peaks are consistent with those (about 345 and 371 nm) in Fig. S2.† As shown in the inset, the luminescence decay curve was exponential, and the decay time was estimated to be  $\sim 27.2$  ns.

There are six distinct excitation bands in the VUV-UV excitation spectrum (the black solid line) in the range of 125–340 nm, which originate from the host-related absorption and the 4f–5d transitions of  $\text{Ce}^{3+}$ . The host related absorption band peaked at  $\sim 170$  nm ( $7.29$  eV,  $58.8 \times 10^3$   $\text{cm}^{-1}$ ) is identified as the host exciton creation absorption energy  $E^{ex}$ . The band gap between the bottom of the conduction band and the top of the valence band is equal to this exciton creation energy plus the exciton binding energy. The empirical formula  $0.008 \times (E^{ex})^2 = 0.43$  eV was used to estimate the exciton binding energy.<sup>16</sup> Then, the band gap of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  was evaluated to be  $\sim 7.72$  eV.

Four clear excitation bands at about 326 nm ( $3.80$  eV,  $30.7 \times 10^3$   $\text{cm}^{-1}$ ), 269 nm ( $4.61$  eV,  $37.2 \times 10^3$   $\text{cm}^{-1}$ ), 244 nm ( $5.08$  eV,  $41.0 \times 10^3$   $\text{cm}^{-1}$ ), and 217 nm ( $5.71$  eV,  $46.1 \times 10^3$   $\text{cm}^{-1}$ ) and a relatively weak band at about 200 nm ( $6.20$  eV,  $50.0 \times 10^3$   $\text{cm}^{-1}$ ) were observed in the 190–340 nm range of the excitation spectrum. These bands are attributed to the five 4f–5d<sub>i</sub> ( $i = 1, 2, \dots, 5$ ) excitation bands of  $\text{Ce}^{3+}$ . The number of observed 4f–5d excitation bands is in good agreement with that of the theoretical prediction of 5d undegenerated orbitals after the crystal field splitting of  $\text{Ce}^{3+}$  in the  $C_1$  low-symmetry [ $\text{SrO}_8$ ] site of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ . Accordingly, the 5d crystal field splitting (CFS) energy of  $\text{Ce}^{3+}$  is evaluated to be about 2.40 eV ( $19.3 \times 10^3$   $\text{cm}^{-1}$ ) and the 5d centroid energy is about 5.08 eV ( $41.0 \times 10^3$   $\text{cm}^{-1}$ ). The 5d centroid energy of  $\text{Ce}^{3+}$  in a compound depends on the covalence between anion ligands and the 5d-orbital, and the spectroscopic polarizability of the anions in the first coordination sphere around  $\text{Ce}^{3+}$ , which are closely related to the nephelauxetic effect.<sup>17</sup> In the present case, the 5d centroid energy of  $\text{Ce}^{3+}$  ( $41.0 \times 10^3$   $\text{cm}^{-1}$ ) is higher than that of silicates like  $\text{Lu}_2\text{Si}_2\text{O}_7$  ( $38.8 \times 10^3$   $\text{cm}^{-1}$ ) and  $\text{Li}_2\text{CaSiO}_4$  ( $39.6 \times 10^3$


$\text{cm}^{-1}$ ).<sup>18,19</sup> Clearly, a relatively higher 5d centroid energy implies a weaker covalence, spectroscopic polarizability and nephelauxetic effect in this case. The 5d CFS of  $\text{Ce}^{3+}$  is significantly affected by the size and shape of the first anion coordination polyhedron around  $\text{Ce}^{3+}$ , especially the symmetry of the site, the coordination number and the  $\text{Ce}^{3+}\text{--O}^{2-}$  bond length. The 5d CFS of  $\text{Ce}^{3+}$  (2.40 eV) in the present case falls in between that of other eight-fold coordinated sites of silicates, such as the  $C_1$  symmetry of  $\text{Ba}^{2+}$  in  $\text{BaMg}_2\text{Si}_2\text{O}_7$  (1.97 eV) and the  $C_2$  symmetry of  $\text{Ca}^{2+}$  in  $\text{CaMgSiO}_6$  (2.61 eV),<sup>5,20</sup> which is in good agreement with the average Ce–O bond length in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  (2.669 Å) between those in  $\text{BaMg}_2\text{Si}_2\text{O}_7$  (2.882 Å) and  $\text{CaMgSiO}_6$  (2.501 Å). With the peaks of the lowest 5d and  $^2F_{5/2}$  transitions in the excitation (326 nm) and emission (345 nm) spectra, the Stokes shift was estimated to be about 0.21 eV ( $1.69 \times 10^3$   $\text{cm}^{-1}$ ), which is smaller than the average value  $\sim 0.31$  eV ( $2.5 \times 10^3$   $\text{cm}^{-1}$ ) of  $\text{Ce}^{3+}$ -doped compounds and suggests a smaller electron-vibrational interaction (EVI) for the 4f–5d transitions of  $\text{Ce}^{3+}$  in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ .

The EVI of a  $\text{Ce}^{3+}$  impurity center is characterized by three parameters, including the Stokes shift, the Huang–Rhys factor ( $S$ ) and the effective phonon energy ( $\hbar\omega$ ). All of them describe the shift of the electronic states corresponding to the ground and excited electronic states. The value of  $S$  and  $\hbar\omega$  can be estimated using eqn (1) and (2):<sup>21</sup>

$$\Delta E_s = (2S - 1)\hbar\omega \quad (1)$$

$$\Gamma(T) = \sqrt{8 \ln 2} \hbar\omega \left[ S \coth\left(\frac{\hbar\omega}{2kT}\right) \right]^{1/2} \quad (2)$$

where  $T$  is the temperature (K),  $\Gamma(T)$  is the full width at half maximum (FWHM) of the emission band at temperature  $T$ , and  $k$  is the Boltzmann constant ( $8.62 \times 10^{-5}$  eV  $\text{K}^{-1}$ ). The  $\Gamma(T)$  of the 5d to  $^2F_{5/2}$  emission band at 78 K was estimated to be  $1380$   $\text{cm}^{-1}$  *via* a Gaussian fit according to the experimental result shown in Fig. 2. With the solution, we can predict the

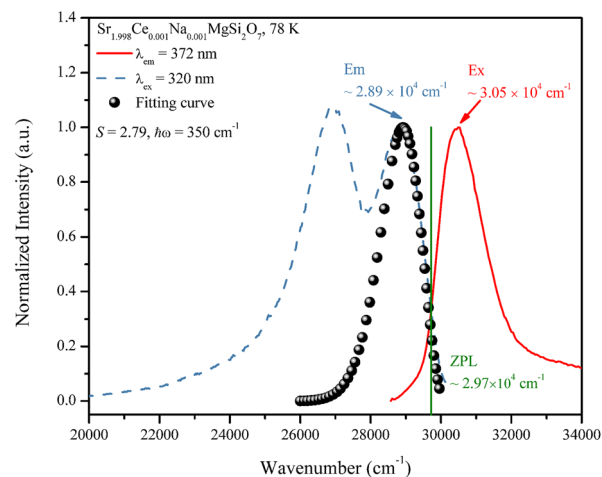

**Fig. 2** The height-normalized excitation ( $\lambda_{em} = 372$  nm) and emission ( $\lambda_{ex} = 320$  nm) spectra of the sample  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  at 78 K and the fitting curve *via* EVI analysis.

emission band of  $\text{Ce}^{3+}$  using eqn (3) and further confirm the solution validity,

$$I = \frac{e^{-S} S^p}{p!} \left( 1 + S^2 \frac{e^{-\frac{\hbar\omega}{kT}}}{p+1} \right), p = \frac{E_0 - E}{\hbar\omega} \quad (3)$$

where  $E_0$  is the zero-phonon line (ZPL) energy and  $p$  is the number of effective phonons involved in the emission transition. The ZPL is located at the point of intersection of the excitation and emission spectra at 337 nm ( $29.7 \times 10^3 \text{ cm}^{-1}$ ) in this case. By solving eqn (1) and (2), the acquired values are  $S = 2.79$  and  $\hbar\omega = 350 \text{ cm}^{-1}$ . With these values, the best simulation of the  $\text{Ce}^{3+}$  emission band is achieved as shown in Fig. 2, which is in good agreement with the emission band shape, illustrating the validities of  $S$  and  $\hbar\omega$  values. The far infrared reflectance spectrum of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  is displayed in Fig. S3.† Peaks in the range of  $480\text{--}1100 \text{ cm}^{-1}$  are attributed to the stretching and bending modes of Si–O–Si, and those below  $480 \text{ cm}^{-1}$  are due to the M–O (M = Sr, Mg) stretching and bending modes.<sup>22</sup> Accordingly, the effective phonons should correspond to the M–O (M = Sr, Mg) stretching and bending vibrations, and the infrared spectrum verifies the validities of the fitted effective phonon energy  $\hbar\omega$ . Such smaller  $S$  and  $\hbar\omega$  values further confirm the weak electron–phonon coupling.


$\text{Ce}^{3+}$  doping concentration dependent luminescence is also studied as shown in Fig. S4 of the ESI.† The nearly identical spectral profiles and overlapped luminescence decay curves indicate that concentration quenching has not occurred yet in the doping range. The lifetime of  $\text{Ce}^{3+}$  at RT shown in Fig. S4(b)† is consistent with that at 78 K shown in the inset of Fig. 1, implying that temperature quenching does not occur below RT, as discussed in detail below.

Fig. 3(a) shows the excitation ( $\lambda_{\text{em}} = 372 \text{ nm}$ ) and emission ( $\lambda_{\text{ex}} = 320 \text{ nm}$ ) spectra of  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  at 78–500 K. The band intensities of excitation and emission decrease significantly with the increase of the temperature. A


careful examination of the excitation spectrum shows that the first excitation peak slightly moves toward the short-wavelength direction (from  $\sim 326 \text{ nm}$  at 78 K to  $\sim 323 \text{ nm}$  at 500 K) as the temperature increases, resulting from the decrease of  $\text{Ce}^{3+}$  5d CFS with the lattice expansion at a higher temperature. Meanwhile, the doublet emission bands gradually merge into one broad band due to the heat-stimulated electron–phonon interaction.

The luminescence decay curves of the sample  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  in Fig. 3(b) nearly overlap each other in the 78–500 K range and conform to the exponential characteristics, which manifests that thermal quenching does not occur within this temperature range, indicating the good thermal stability of  $\text{Ce}^{3+}$  luminescence. This can be further corroborated by the vacuum referred binding energy (VRBE) scheme of lanthanide ions in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  as follows.

By using the experimental data including the band gap energy (7.72 eV, arrow A in Fig. 4), the centroid energy of  $\text{Ce}^{3+}$  5d states (5.08 eV) and the lowest 5d excitation energy of  $\text{Ce}^{3+}$  (3.80 eV, arrow B) obtained above, as well as the  $\text{Eu}^{3+}\text{--O}^{2-}$  charge transfer energy (4.96 eV, arrow C) from Fig. S5,† the U value, which corresponds to the energy between  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  ground states, was calculated to be about 7.03 eV, and the VRBE scheme of the 4f ground states and the first 5d excited states of all trivalent and divalent lanthanide ions in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  can be constructed as displayed in Fig. 4. It can be found that the energy difference ( $E_{\text{dc}}$ ) between the lowest 5d multiplet ( $5d_1$ ) of  $\text{Ce}^{3+}$  and the conduction band minimum of  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  is  $\sim 0.53 \text{ eV}$ , which is larger than those in silicates such as  $\text{Sr}_2\text{Al}_2\text{SiO}_7$  (0.45 eV) and  $\text{SrB}_2\text{Si}_2\text{O}_8$  (0.21 eV), implying the better luminescence thermal stability of  $\text{Ce}^{3+}$  in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  provided that thermal-ionization is the main cause for luminescence thermal-quenching.<sup>23,24</sup> In addition, the

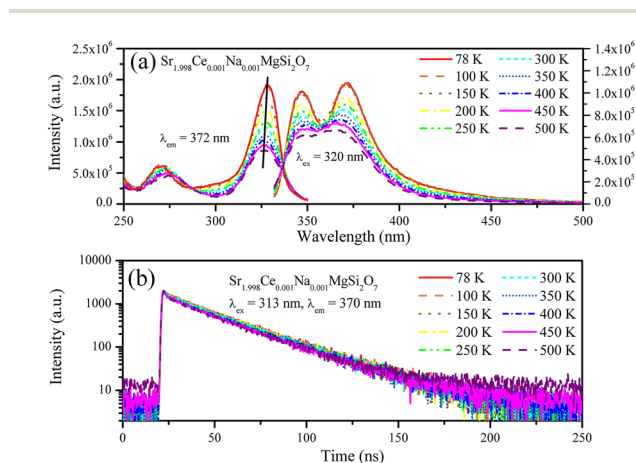

**Fig. 3** (a) The excitation ( $\lambda_{\text{em}} = 372 \text{ nm}$ ) and emission ( $\lambda_{\text{ex}} = 320 \text{ nm}$ ) spectra and (b) luminescence decay curves ( $\lambda_{\text{ex}} = 313 \text{ nm}$ ,  $\lambda_{\text{em}} = 370 \text{ nm}$ ) of the  $\text{Sr}_{1.998}\text{Ce}_{0.001}\text{Na}_{0.001}\text{MgSi}_2\text{O}_7$  sample in the temperature range of 78 to 500 K.

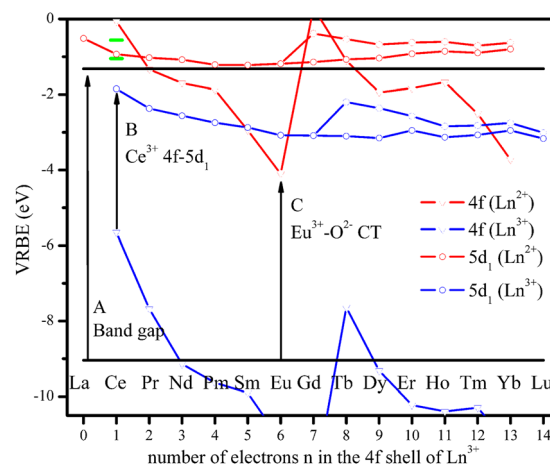

**Fig. 4** The vacuum referred binding energy (VRBE) scheme of all trivalent and divalent lanthanide ( $\text{Ln}^{3+}$  and  $\text{Ln}^{2+}$ ) ions in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ . The upper solid line is the conduction band minimum (CBM) and the lower one is the valence band maximum (VBM). The blue lines are the 4f ground states and the lowest 5d states of  $\text{Ln}^{3+}$ , while the red lines are related to  $\text{Ln}^{2+}$ . The green horizontal bars are  $5d_2$  and  $5d_3$  of  $\text{Ce}^{3+}$ .

short green bars in Fig. 4 depict the second and third 5d excitation states ( $5d_2$ ,  $5d_3$ ) of  $Ce^{3+}$  in the compound, which are located in the conduction band. This explains the weak excitation band intensities of the  $4f-5d_{2,3,4,5}$  transitions in relation to the unambiguously intense  $4f-5d_1$  transition shown in Fig. 1 due to the auto-ionization processes of electrons in these higher  $5d_{2,3,4,5}$  excited states.<sup>13</sup>

### 3.3. Impact of the local structure on the luminescence of $Ce^{3+}$ in $Sr_2MgSi_2O_7$ , $Ba_2MgSi_2O_7$ and $BaMg_2Si_2O_7$

$Sr_2MgSi_2O_7$ ,  $Ba_2MgSi_2O_7$  and  $BaMg_2Si_2O_7$  are three typical alkaline earth pyrosilicates with similar compositions.<sup>20,25</sup> In these compounds, there is only one type of eight-fold coordinated  $Ba^{2+}$  or  $Sr^{2+}$  site with  $C_1$  symmetry as listed in Table 1. The doped  $Ce^{3+}$  ions are expected to enter  $Ba^{2+}$  or  $Sr^{2+}$  sites but not occupy  $Mg^{2+}$  sites because the ionic radius of  $Mg^{2+}$  is evidently smaller than that of  $Ce^{3+}$ . Based on these structural characteristics, they should be suitable compounds to understand the dependence of luminescence properties on the local structure of  $Ce^{3+}$  in the host compounds. It is of significance to compare the structure and the band gap of the three host compounds and discuss their impact on luminescence properties such as the 5d centroid energy, the Stokes shift, the 5d CFS and the decay time of  $Ce^{3+}$  in these host compounds.

Firstly, we discuss the band gap and the band structure. From the data in Table 1, it can be found that the wavelength of the exciton peak slowly increases according to the relative order  $BaMg_2Si_2O_7$  (162 nm) <  $Sr_2MgSi_2O_7$  (170 nm) <  $Ba_2MgSi_2O_7$  (180 nm), while the estimated band gap energy certainly follows the opposite sequence  $BaMg_2Si_2O_7$  (8.12 eV) >  $Sr_2MgSi_2O_7$  (7.72 eV) >  $Ba_2MgSi_2O_7$  (7.27 eV). The mean band gap energy of the three compounds was calculated to be  $7.70 \pm 0.42$  eV. The band gap is thought to be strongly dependent on the compound composition and structure. The density functional theory (DFT) study of  $Ba_2MgSi_2O_7$  indicates that the valence band maximum (VBM) is dominated by O 2p states, and the conduction band minimum (CBM) is mainly formed by Ba 5d states with a small contribution from O 2p states through Ba–O bonding.<sup>26</sup> We speculate that the other two compounds also have similar band structures because of their

similar layered structures and band gaps. The difference in the alkaline earth cations forming a single layer in the layered structure may be responsible for the slight alteration of the band gap among these three cases.<sup>27</sup>

Then we deal with the 5d centroid energy and the Stokes shift of  $Ce^{3+}$ . A fascinating phenomenon that the sequence of the 5d centroid energy of  $Ce^{3+}$  is consistent with the order of band gap values is found in Table 1. It shows that the wider the band gap is, the higher the 5d centroid of  $Ce^{3+}$  is. As mentioned above, the 5d centroid of  $Ce^{3+}$  is closely related to the covalence between anion ligands and the 5d-orbital of  $Ce^{3+}$ , the spectroscopic polarizability of the anions in the first coordination sphere around  $Ce^{3+}$  and/or the nephelauxetic effect. This observation seems to imply that the covalence/spectroscopic polarizability/nephelauxetic effect affects the band gap through bonding strength, but more examples need to be taken into account. Besides, the Stokes shift of the  $Ce^{3+}$   $4f-5d$  transition seems to increase with the decrease of the band gap of the host compound, showing that the electron-vibrational interaction is getting weaker from  $Ba_2MgSi_2O_7$  to  $Sr_2MgSi_2O_7$  and  $BaMg_2Si_2O_7$ , which further proves that the large band gap is associated with strong bonding.

Thirdly, it can be noted that the increase in the sequence of  $Ce^{3+}$  5d CFS energy in the order of  $BaMg_2Si_2O_7$  (1.97 eV) <  $Ba_2MgSi_2O_7$  (2.02 eV) <  $Sr_2MgSi_2O_7$  (2.40 eV) is in good agreement with the decrease in the sequence of average M–O (M = Ba or Sr) bond lengths in the order of  $BaMg_2Si_2O_7$  (2.884 Å) >  $Ba_2MgSi_2O_7$  (2.813 Å) >  $Sr_2MgSi_2O_7$  (2.669 Å). Because the  $Ce^{3+}$  ions occupy the  $C_1$  symmetry  $[MO_8]$  (M = Ba or Sr) sites in all three cases, the magnitude of  $Ce^{3+}$  5d CFS is mainly decided by the site size herein. The larger the  $M^{2+}$  site size, the longer the average M–O bond length, and the smaller the  $Ce^{3+}$  5d CFS energy.

Finally, we compare the luminescence decay time of  $Ce^{3+}$  in three cases. Fig. S6† displays a good linear relationship of  $\lambda^3$  vs.  $\tau$  for  $Ce^{3+}$  in  $Sr_2MgSi_2O_7$ ,  $Ba_2MgSi_2O_7$  and  $BaMg_2Si_2O_7$ , where  $\lambda$  (nm) is the emission peak wavelength of the  $5d-2F_{5/2}$  transition derived from Table 1 and  $\tau$  (s) represents its luminescence decay time. It is widely accepted that luminescence decay is positively correlated with the emission wavelength, and the polarization effect or the local-field effect that has

**Table 1** The host structure and luminescence of  $Ce^{3+}$  in  $Sr_2MgSi_2O_7$ ,  $Ba_2MgSi_2O_7$  and  $BaMg_2Si_2O_7$

Host compound	$Sr_2MgSi_2O_7$	$Ba_2MgSi_2O_7$	$BaMg_2Si_2O_7$
Crystal system	Tetragonal ( $P421m$ )	Orthorhombic ( $C2/c$ )	Orthorhombic ( $C2/c$ )
Coordination number of $Sr^{2+}/Ba^{2+}$ ions	8	8	8
Symmetry of $Sr^{2+}/Ba^{2+}$ sites	$C_1$	$C_1$	$C_1$
Average bond length of $Sr^{2+}/Ba^{2+}-O^{2-}$ (Å)	2.669	2.813	2.884
Exciton peak (nm)	170	180	162
Band gap (eV)	7.72	7.27	8.12
$Ce^{3+}$ 5d energy (eV)	3.80, 4.61, 5.08, 5.71, 6.20	4.00, 4.25, 4.88, 5.69, 6.02	4.17, 4.48, 5.08, 5.71, 6.14
$Ce^{3+}$ 5d centroid energy (eV)	5.08	4.97	5.12
$Ce^{3+}$ 5d CFS (eV)	2.40	2.02	1.97
$Ce^{3+}$ emission (eV)	3.34, 3.59	3.44, 3.69	3.73, 4.00
$Ce^{3+}$ Stokes shift (eV)	0.21	0.31	0.17
$Ce^{3+}$ decay time (ns)	27.2	25	19.2

been used to interpret the various lifetimes of the  $\text{Ce}^{3+}$  4f–5d emissions in different media with the following formulas:<sup>28</sup>

$$\frac{1}{\tau_r} = 4.34 \times 10^{17} \times |\langle 5d|r|4f \rangle_{\text{eff}}|^2 \chi \times \frac{1}{\lambda^3} \quad (4)$$

$$\chi = n \left[ \frac{(n^2 + 2)}{3} \right]^2 \quad (5)$$

where  $\tau_r$  is the radiative lifetime (s),  $\lambda$  is the emission wavelength of  $\text{Ce}^{3+}$ ,  $\langle 5d|r|4f \rangle_{\text{eff}}$  is the effective radial integral with a best-fit value of 0.0281 nm for  $\text{Ce}^{3+}$ ,  $\chi$  is the enhancement factor in the virtual cavity model and  $n$  is the refractive index of the compound. Due to the good  $\lambda^3 - \tau$  linear relationship, we assume that the refractive indexes of the three pyrosilicate compounds are almost the same. Accordingly, the (average)  $\chi$  value is fitted to be about 4.44. The (average) refractive index of these pyrosilicates is further estimated to be 1.69, which is slightly smaller than that (1.71) of those pyrosilicates mentioned in ref. 29.

### 3.4. Photoluminescence of $\text{Eu}^{2+}$ in $\text{Sr}_2\text{MgSi}_2\text{O}_7$

Fig. 5 depicts the synchrotron radiation VUV-UV excitation ( $\lambda_{\text{em}} = 470$  nm, red dashed line) and emission ( $\lambda_{\text{ex}} = 355$  nm, black solid line) spectra at 11 K, and the lab UV-vis excitation spectrum ( $\lambda_{\text{em}} = 470$  nm, blue dash dotted line) of the sample  $\text{Sr}_{1.999}\text{Eu}_{0.001}\text{MgSi}_2\text{O}_7$  at 78 K, respectively. The two spectra are in line in the 320–345 nm region. The bands in the 200–450 nm range are attributed to the 4f–5d transitions of  $\text{Eu}^{2+}$ , and those above this region are attributed to host-related absorption as mentioned in Fig. 1. The host exciton creation peak at about 172 nm is in good agreement with that observed in Fig. 1.

The sample exhibits intense cyan emission peaking at ~470 nm (2.64 eV), and its FWHM is  $\sim 1.69 \times 10^3 \text{ cm}^{-1}$  (0.209 eV). The energy of transition from the ground 4f multiplet to

the first 5d level ( $5d_1$ ) of  $\text{Eu}^{2+}$  is empirically estimated to be ~435 nm (2.85 eV) in terms of the wavelength at 15 to 20% of the maximum excitation intensity on the long-wavelength side.<sup>30</sup> Accordingly, the Stokes shift of  $\text{Eu}^{2+}$  emission was found to be ~0.21 eV, which will be used later to discuss the luminescence thermal-quenching channels. The decay curve in the inset is exponential with a decay time of ~572 ns.

Fig. 6 shows the intensity normalized emission spectra (a,  $\lambda_{\text{ex}} = 355$  nm) and luminescence decay curves (b,  $\lambda_{\text{ex}} = 340$  nm,  $\lambda_{\text{em}} = 470$  nm) of the sample  $\text{Sr}_{1.999}\text{Eu}_{0.001}\text{MgSi}_2\text{O}_7$  at 78–450 K, respectively. The emission bands broaden steadily and the integrated intensities decrease with an increase in temperature (Fig. 6(a and c)), while the emission peaks shift by about 4 nm to the short-wavelength side. Meanwhile, the luminescence decays become rapid and start to deviate from exponential gradually (Fig. 6(b)). The evolution of decay curves implies the occurrence of thermal quenching of  $\text{Eu}^{2+}$  emission in the temperature range. The curves (c and d) display the dependencies of the integrated emission intensity and lifetime on temperature. The variations of the integrated intensity and lifetime show similar tendencies, which further confirms the earlier result.<sup>31</sup> According to the single-barrier-quenching model, the thermal quenching activation energy ( $E_a$ ) of  $\text{Eu}^{2+}$  luminescence is estimated using eqn (6) and (7), respectively,<sup>32</sup>


$$I(T) = \frac{I_0}{1 + \Gamma_0/\Gamma_v \exp(-E_a/kT)} \quad (6)$$

$$\tau(T) = \frac{1/\Gamma_v}{1 + \Gamma_0/\Gamma_v \exp(-E_a/kT)} \quad (7)$$

where  $I(T)$  and  $\tau(T)$  are the integrated intensity and luminescence lifetime at temperature  $T$ , respectively,  $I_0$  is the initial integrated intensity,  $\Gamma_0$  is the thermal-quenching rate at  $T = \infty$ ,  $\Gamma_v$  is the reciprocal of the intrinsic lifetime of  $\text{Eu}^{2+}$ , and  $k$  is the Boltzmann constant ( $8.62 \times 10^{-5} \text{ eV K}^{-1}$ ). The fitting results derived from the integrated intensity and lifetime are listed in Table S1.†  $\Gamma_v$  values are fitted as  $1.73 \times 10^6$  and  $1.76 \times 10^6 \text{ s}^{-1}$ , respectively, corresponding to the intrinsic lifetimes of 578 ns and 568 ns, which is consistent with the data (572 ns) obtained from the decay curve at 78 K. Besides, the thermal quenching activation energy ( $E_a$ ) values were evaluated to be 0.226 and 0.252 eV, respectively. So the mean  $E_a$  value was calculated to be  $0.239 \pm 0.013 \text{ eV}$ .


The thermal quenching mechanism of  $\text{Eu}^{2+}$  luminescence in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$  can be understood with the help of this activation energy ( $E_a$ ). The luminescence thermal quenching of 4f–5d transitions is thought to be the consequence of one of the following three mechanisms or their combinations:<sup>33</sup> (1) crossover relaxation (CR) caused by electron–phonon coupling, (2) thermally activated concentration quenching, and (3) thermal ionization of 5d electrons into the conduction band.

Firstly, the 4f–5d CR mechanism can be excluded from the present case. The energy barrier for the CR channel ( $E_{\text{fd}}$ ) has been estimated to be about 2.14 eV using the first-principles study.<sup>34</sup> Such a large difference between the values of  $E_{\text{fd}}$  (2.14 eV) and  $E_a$  ( $0.239 \pm 0.013 \text{ eV}$ ) strongly negates the possibility of

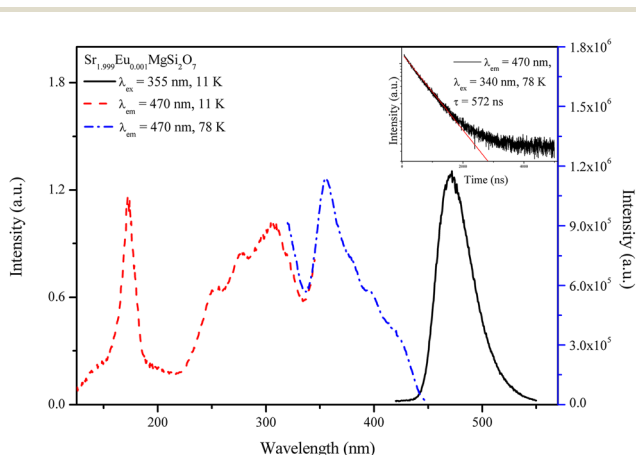

**Fig. 5** The synchrotron radiation VUV-UV excitation (red dashed line,  $\lambda_{\text{em}} = 470$  nm) and emission (black solid line,  $\lambda_{\text{ex}} = 355$  nm) spectra at 11 K and UV-vis excitation spectra (blue dash dot line,  $\lambda_{\text{em}} = 470$  nm) at 78 K of the  $\text{Sr}_{1.999}\text{Eu}_{0.001}\text{MgSi}_2\text{O}_7$  sample. The inset shows the luminescence decay curve ( $\lambda_{\text{ex}} = 340$  nm,  $\lambda_{\text{em}} = 470$  nm) at 78 K.



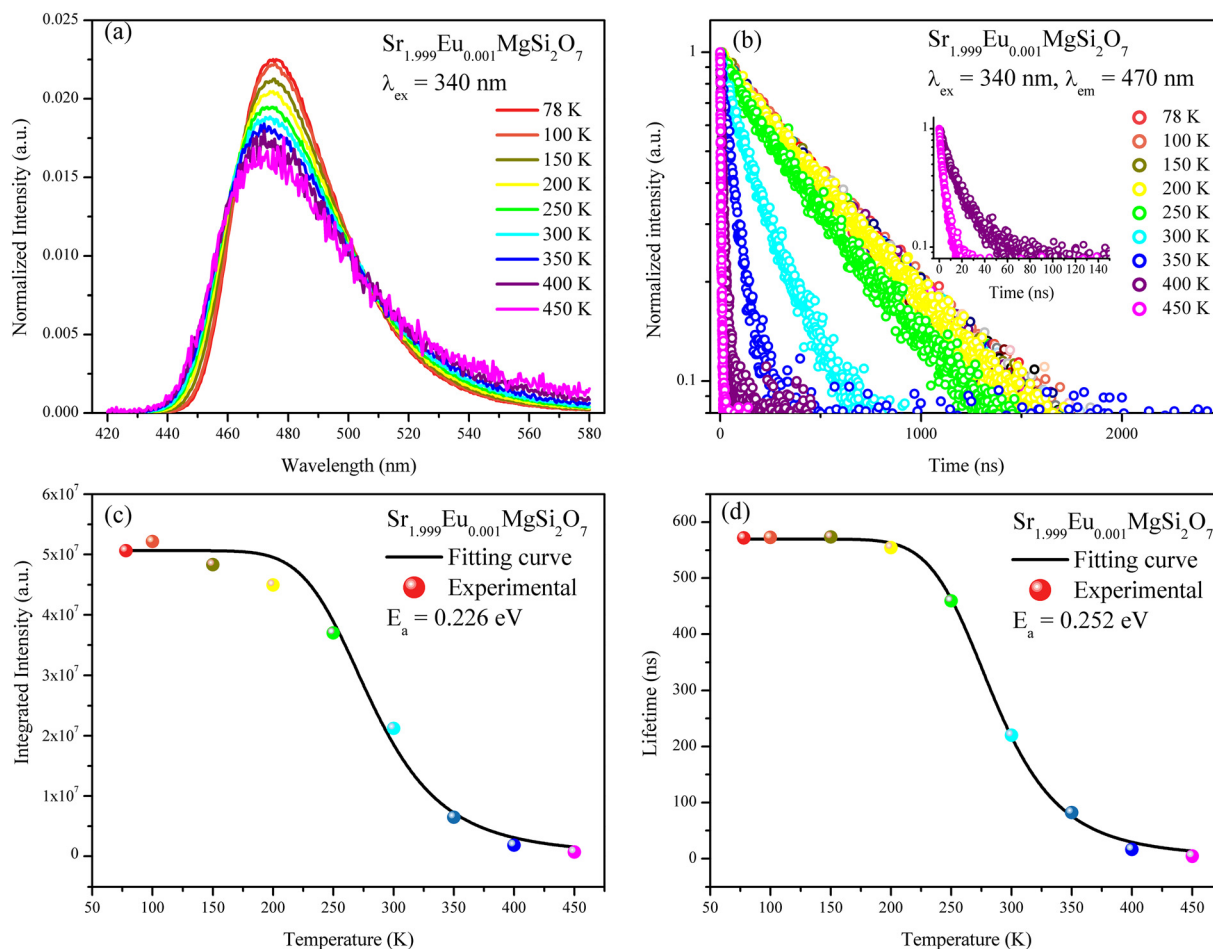


**Fig. 6** (a) The intensity normalized emission spectra ( $\lambda_{\text{ex}} = 355$  nm) and (b) normalized luminescence decay curves ( $\lambda_{\text{ex}} = 340$  nm,  $\lambda_{\text{em}} = 470$  nm) of the  $\text{Sr}_{1.999}\text{Eu}_{0.001}\text{MgSi}_2\text{O}_7$  sample in the temperature range of 78–450 K. The inset in plot b shows the details of the decay curve at 400 K and 450 K. The dependencies of the integrated emission intensity (c) and lifetime (d) on temperature and the fitting curves using eqn (6) and (7).

CR as the channel for the luminescence thermal quenching of  $\text{Eu}^{2+}$  in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ . Besides, we assume that the thermally activated concentration quenching is also not the dominant channel for the thermal quenching of  $\text{Eu}^{2+}$  luminescence, due to the small overlap between the excitation and emission bands as shown in Fig. 5. Accordingly, the thermal ionization of 5d electrons in the conduction band should play an important role in the thermal quenching of  $\text{Eu}^{2+}$  luminescence processes. The VRBE scheme shown in Fig. 4 can illustrate the rationality of this viewpoint. The energy barrier between the lowest 5d of  $\text{Eu}^{2+}$  and the conduction band minimum ( $E_{\text{dc}}$ ) is a vital parameter for thermal ionization processes. It can be found that there is only a small difference between  $E_{\text{dc}}$  (about  $-0.14$  eV) read from the VRBE scheme in Fig. 4 and the above-mentioned  $E_{\text{a}}$  value ( $0.239 \pm 0.013$  eV). This smaller  $E_{\text{dc}}$  value may be related to the introduction of errors in the processes of measuring luminescence and building the VRBE scheme.<sup>35</sup> Besides, the measurement of luminescence and the fitting of the activation energy may also result in some errors. These factors are responsible for the discrepancies between the two estimates. Although there is a difference between the  $E_{\text{dc}}$  and

$E_{\text{a}}$  values, the VRBE scheme in Fig. 4 gives us a crucial indication that the lowest 5d of  $\text{Eu}^{2+}$  is close to the conduction band minimum. It is reasonable that thermal ionization is considered to be the most likely major mechanism for thermal quenching of  $\text{Eu}^{2+}$  luminescence in our case.

### 3.5. Energy transfer dynamics of $\text{Ce}^{3+}$ and $\text{Eu}^{2+}$ in $\text{Sr}_2\text{MgSi}_2\text{O}_7$

The discussions in sections 3.2 and 3.3 manifest the spectral overlap between the excitation bands of  $\text{Ce}^{3+}$  and the emission bands of  $\text{Eu}^{2+}$ , implying that  $\text{Ce}^{3+}$  ions can serve as a possible sensitizer to the luminescence of  $\text{Eu}^{2+}$  ions through energy transfer. To verify the ET from  $\text{Ce}^{3+}$  to  $\text{Eu}^{2+}$ , the luminescence properties of a series of  $\text{Ce}^{3+}$  and  $\text{Eu}^{2+}$  co-doped samples  $\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_x\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  ( $x = 0, 0.001, 0.005, 0.01$ ) with a fixed  $\text{Ce}^{3+}$  concentration were measured and are shown in Fig. 7. With the increase of the  $\text{Eu}^{2+}$  concentration, the emission intensities of  $\text{Ce}^{3+}$  drop sharply and the decay curves of  $\text{Ce}^{3+}$  gradually deviate from the exponential, implying the appearance of energy transfer from  $\text{Ce}^{3+}$  to  $\text{Eu}^{2+}$ . To further study the energy transfer dynamics from  $\text{Ce}^{3+}$  to  $\text{Eu}^{2+}$ , the

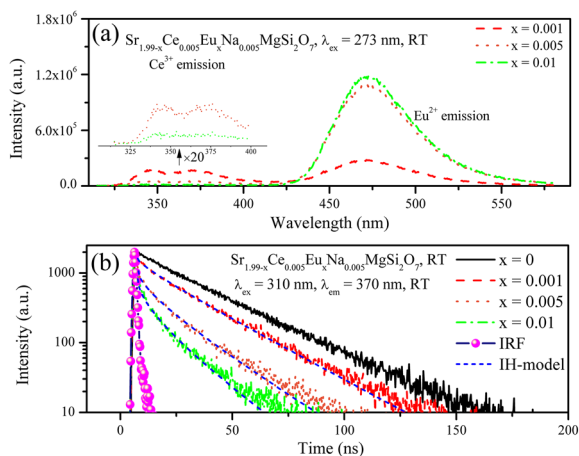

**Fig. 7** (a) The emission spectra ( $\lambda_{\text{ex}} = 273$  nm) of the samples  $\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_{0.001}\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  ( $x = 0, 0.001, 0.005, 0.01$ ) and (b) luminescence decay curves ( $\lambda_{\text{ex}} = 310$  nm,  $\lambda_{\text{em}} = 370$  nm) of the samples  $\text{Sr}_{1.99-x}\text{Ce}_{0.005}\text{Eu}_{0.001}\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  ( $x = 0.001, 0.005, 0.01$ ) at RT and the fitting result using the Inokuti–Hirayama (IH) model ( $S = 6$ ).

decay curve of the sample  $\text{Sr}_{1.989}\text{Ce}_{0.005}\text{Eu}_{0.001}\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  is fitted by three models as follows.


First, we only consider the energy transfer between the donor  $\text{Ce}^{3+}$  and the acceptor  $\text{Eu}^{2+}$  when energy migration between the donor  $\text{Ce}^{3+}$  ions does not exist, and the decay

$$I(t) = I(0) \exp \left[ -\left( \frac{t}{\tau_0} \right) - \frac{4\pi}{3} C_A \Gamma \left( 1 - \frac{3}{S} \right) (C_{\text{DA}} t)^{\frac{3}{S}} \times \left( \frac{1 + 10.866X + 15.500X^2}{1 + 8.743X} \right)^{\frac{S-3}{S-2}} \right] \quad (9)$$

curve behavior can be described with the Inokuti–Hirayama (IH) model listed below,<sup>36</sup>

$$I(t) = I(0) \exp \left[ -\left( \frac{t}{\tau_0} \right) - \frac{4\pi}{3} C_A \Gamma \left( 1 - \frac{3}{S} \right) (C_{\text{DA}} t)^{\frac{3}{S}} \right] \quad (8)$$

where  $I(0)$  and  $I(t)$  are the initial luminescence intensity and the emission intensity of  $\text{Ce}^{3+}$  at time  $t$ , respectively;  $\tau_0$  is the intrinsic luminescence lifetime of the donor  $\text{Ce}^{3+}$  (27.2 ns);  $C_A$  is the concentration of the acceptor  $\text{Eu}^{2+}$  ( $6.067 \times 10^{24} \text{ m}^{-3}$ );  $C_{\text{DA}}$  is the energy transfer microparameter;  $\Gamma(1 - 3/S)$  is a gamma function;  $S$  is the multipolar effect parameter and its values are 6, 8 and 10, corresponding to the dominant mechanism being electric dipole–dipole, electric dipole–quadrupole or electric quadrupole–quadrupole interactions, respectively. To identify the main mechanism of multipolar interaction, the decay curve of the sample  $\text{Sr}_{1.989}\text{Ce}_{0.005}\text{Eu}_{0.001}\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  is fitted using the Inokuti–Hirayama model with different  $S$  values, and the results are shown in Fig. 8 and Table S2.† The best fitting result ( $R^2 = 0.998$ ) is obtained when  $S = 6$ , suggesting that the main mechanism of energy transfer between  $\text{Ce}^{3+}$  and  $\text{Eu}^{2+}$  is the electric dipole–dipole interaction. The  $C_{\text{DA}}$  value was estimated to be  $2.89 \times 10^{-45} \text{ m}^6 \text{ s}^{-1}$  and the critical distance  $R_c$  was found to be 20.7 Å using the relation-

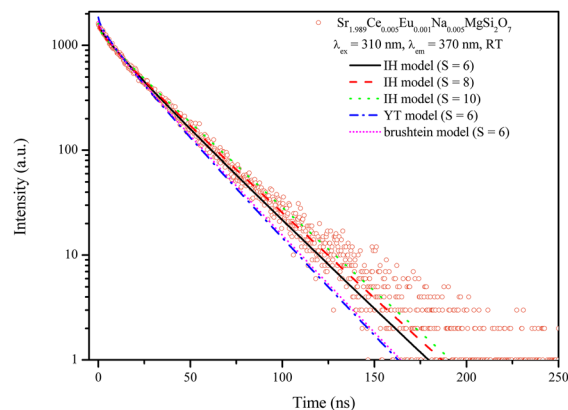

**Fig. 8** The luminescence decay curve ( $\lambda_{\text{ex}} = 310$  nm,  $\lambda_{\text{em}} = 370$  nm) of the  $\text{Sr}_{1.989}\text{Ce}_{0.005}\text{Eu}_{0.001}\text{Na}_{0.005}\text{MgSi}_2\text{O}_7$  sample at RT and the corresponding fitting curves using the Inokuti–Hirayama model ( $S = 6, 8, 10$ ), Yokota–Tanimoto model ( $S = 6$ ) and Burshtein model ( $S = 6$ ).

ship  $\tau_0 = R_c^S / C_{\text{DA}}^{(S)}$ , which implies that the energy transfer from  $\text{Ce}^{3+}$  to  $\text{Eu}^{2+}$  is effective.

In addition, the energy migration between the donor  $\text{Ce}^{3+}$  is analyzed and carefully excluded. When the distance between adjacent  $\text{Ce}^{3+}$  ions is shorter than that between the  $\text{Ce}^{3+}$  and  $\text{Eu}^{2+}$  ions, a slow energy migration may come up between  $\text{Ce}^{3+}$  and the luminescence of donor  $\text{Ce}^{3+}$  can be described using the Yokota–Tanimoto (YT) model (diffusion model),<sup>37</sup>

$$X = D \times C_{\text{DA}}^{-\frac{2}{S}} \times t^{\frac{S-2}{S}} \quad (10)$$

$$D = \frac{C_{\text{DD}}}{2(S-5)} \times \left( \frac{4\pi C_{\text{D}}}{3} \right)^{\frac{S-2}{S}} \quad (11)$$

where  $D$  is the diffusion parameter,  $C_{\text{DD}}$  is the energy migration parameter,  $C_{\text{D}}$  is the concentration of donor  $\text{Ce}^{3+}$  ( $3.034 \times 10^{25} \text{ m}^{-3}$ ) and other symbols have the same meaning as above. The fitting result is also displayed in Fig. 8 and Table S2.†  $C_{\text{DA}}$  was fitted to be  $2.35 \times 10^{-46} \text{ m}^6 \text{ s}^{-1}$  while  $C_{\text{DD}}$  was  $1.03 \times 10^{-45} \text{ m}^6 \text{ s}^{-1}$ . This result does not meet the constraint of the Yokota–Tanimoto model that  $C_{\text{DD}} \ll C_{\text{DA}}$ , which reveals that the slow energy migration between  $\text{Ce}^{3+}$  is invalid.

Finally, the Burshtein model (hopping model) is applied to estimate the fast energy migration between  $\text{Ce}^{3+}$ ,<sup>38</sup>

$$I(t) = I(0) \exp \left[ -\left( \frac{t}{\tau_0} \right) - \frac{4\pi}{3} C_A \Gamma \left( 1 - \frac{3}{S} \right) (C_{\text{DA}} t)^{\frac{3}{S}} - Wt \right] \quad (12)$$

where  $W = \pi \left( \frac{2\pi}{3} \right)^{\frac{5}{2}} C_A^2 (C_{\text{DA}} C_{\text{DD}})^{\frac{1}{2}}$  and other symbols are the same as those mentioned above. The fitting result is presented

in Fig. 8 and Table S2,<sup>†</sup> but  $C_{DA}$  and  $C_{DD}$  failed to satisfy the validity rule of the Burshtein model ( $C_{DD} \gg C_{DA}$ ). Therefore, a conclusion can be drawn that the energy transfer between  $Ce^{3+}$  and  $Eu^{2+}$  is mainly governed by the electric dipole-dipole interaction in the sample  $Sr_{1.989}Ce_{0.005}Eu_{0.001}Na_{0.005}MgSi_2O_7$  and the influence of energy migration between  $Ce^{3+}$  in a fast or slow mode is negligible. Besides, when the concentration of  $Eu^{2+}$  is further increased to  $x = 0.005$  and  $0.01$  in the  $Sr_{1.99-x}Ce_{0.005}Eu_xNa_{0.005}MgSi_2O_7$  samples, the luminescence decay curves of  $Ce^{3+}$  are also well described using the Inokuti-Hirayama model, as shown in Fig. 7(b).

### 3.6. X-ray radioluminescence of $Ce^{3+}$ and $Eu^{2+}$ in $Sr_2MgSi_2O_7$


Fig. 9 shows the X-ray excited luminescence spectra of the  $Sr_{1.994}Ce_{0.003}Na_{0.003}MgSi_2O_7$  and  $Sr_{1.997}Eu_{0.003}MgSi_2O_7$  samples at RT. To estimate the absolute light yield under X-ray excitation of these samples, a  $BaF_2$  crystal is measured under the same experimental conditions.<sup>13</sup> The  $BaF_2$  crystal presents typical self-trapped exciton emission with two bands with their maxima at  $\sim 300$  and  $220$  nm, respectively, and its integrated intensity is specified as  $8.80 \times 10^3$  ph  $MeV^{-1}$ .

The emission spectrum of the  $Eu^{2+}$  doped sample under X-ray excitation is in good agreement with that under VUV-UV excitation, and a series of extremely weak sharp peaks in the range of  $550$ – $750$  nm are due to incomplete reduction of  $Eu^{3+}$  ions, but the XEL spectrum of the  $Ce^{3+}$  doped sample is somewhat different from the photoluminescence (PL) spectrum. An additional emission band above  $400$  nm with a peak at about  $450$  nm appears in the XEL spectrum but it is not observed in the PL spectrum. This additional band may be related to the emission of  $Ce^{3+}$  in impurities not detected by XRD or defects under high-energy X-ray excitation. Its integrated intensity was evaluated to be about  $49.2\%$  of the total emission by fitting the XEL spectrum of  $Ce^{3+}$  with a sum of three Gaussian functions [ $Ce^{3+} 5d-2F_J$  ( $J = 5/2, 7/2$ ) bands and the additional  $450$  nm

emission]. According to the measured light output value of  $2.81 \times 10^3$  ph  $MeV^{-1}$ , the light yield of the  $Sr_{1.994}Ce_{0.003}Na_{0.003}MgSi_2O_7$  sample was estimated to be  $1.47 \times 10^3$  ph  $MeV^{-1}$  after subtracting the  $450$  nm emission, and that of the  $Sr_{1.997}Eu_{0.003}MgSi_2O_7$  sample was found to be about  $5.97 \times 10^3$  ph  $MeV^{-1}$ . The low light output implies that these materials are not suitable X-ray detecting phosphors.

## 4. Conclusions

This paper studies the  $4f-5d$  transitions and the energy transfer of  $Ce^{3+}$  and  $Eu^{2+}$  in  $Sr_2MgSi_2O_7$  after the preparation of the samples by a traditional high-temperature solid-state reaction method. (1) The synchrotron radiation VUV-UV excitation spectrum of the sample  $Sr_{1.998}Ce_{0.001}Na_{0.001}MgSi_2O_7$  at  $10$  K reveals that the five  $4f-5d_i$  ( $i = 1, 2, \dots, 5$ ) transitions of  $Ce^{3+}$  in the  $C_1$  low-symmetry [ $SrO_8$ ] site of  $Sr_2MgSi_2O_7$  are located at about  $326, 269, 244, 217$  and  $200$  nm, respectively, and the band intensities can be explained using the vacuum referred binding energy (VRBE) scheme. Typical doublet emission bands of  $Ce^{3+}$  are found with their maxima at about  $345$  and  $368$  nm, and the luminescence decay time is about  $27.2$  ns. The electron-vibrational interaction (EVI) analysis shows that the Huang-Rhys factor ( $S$ ) and the effective phonon energy ( $\hbar\omega$ ) are  $S = 2.79$  and  $\hbar\omega = 350$   $cm^{-1}$  for the  $4f-5d$  transitions of  $Ce^{3+}$  in  $Sr_2MgSi_2O_7$ , respectively. The measurements on the luminescence decay behaviours show that concentration quenching does not occur in  $Sr_{2-2x}Ce_xNa_xMgSi_2O_7$  samples for  $x$  values within  $0.03$ , and the  $Sr_{1.998}Ce_{0.001}Na_{0.001}MgSi_2O_7$  sample does not undergo thermal quenching below  $500$  K. Comparison of the luminescence properties of  $Ce^{3+}$  in a series of host compounds  $Sr_2MgSi_2O_7$ ,  $Ba_2MgSi_2O_7$  and  $BaMg_2Si_2O_7$  with similar compositions indicates that the crystal field splitting (CFS) of  $Ce^{3+} 5d$  increases with the decrease of the site size, while the  $5d$  centroid energy of  $Ce^{3+}$  and the Stokes shift are closely associated with the band gap. The third power of the emission wavelength of  $Ce^{3+}$  in three compounds shows a good linear relationship with the luminescence decay time, which may be related to similar refractive indexes of these pyro-silicates. (2) The  $4f-5d$  excitation bands of  $Eu^{2+}$  covers the  $200$ – $450$  nm range, the cyan emission peaks at about  $470$  nm ( $2.64$  eV) with a FWHM of around  $1687$   $cm^{-1}$  and the decay time is approximately  $572$  ns. The thermal quenching activation energy of  $Eu^{2+}$  luminescence was estimated to be about  $0.239 \pm 0.013$  eV by the dependencies of the lifetime and intensity on temperature. Accordingly, the thermal ionization mechanism is thought to be the main thermal quenching channel. (3) Systematic studies of the luminescence decay curves with three luminescence dynamic models suggest that the energy transfer from  $Ce^{3+}$  to  $Eu^{2+}$  is mainly through electric dipole-dipole interactions and the energy migration between  $Ce^{3+}$  in a fast or slow mode is negligible. (4) The low light outputs of the  $Ce^{3+}$  and  $Eu^{2+}$  doped materials under X-ray exci-

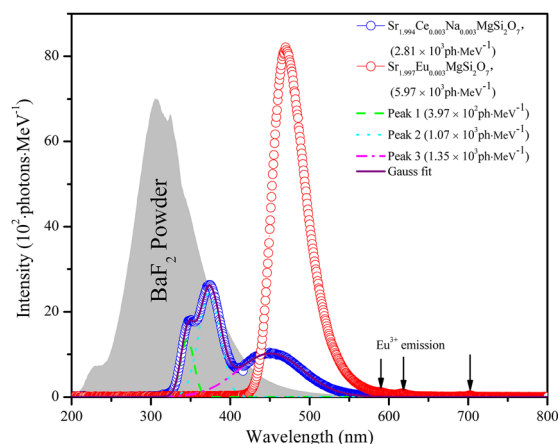

**Fig. 9** The XEL spectra of the samples  $Sr_{1.994}Ce_{0.003}Na_{0.003}MgSi_2O_7$ ,  $Sr_{1.997}Eu_{0.003}MgSi_2O_7$  and crystal  $BaF_2$  at RT, and the Gaussian fitting of the XEL spectrum of  $Sr_{1.994}Ce_{0.003}Na_{0.003}MgSi_2O_7$ .

tation suggest that phosphors are not suitable for X-ray detection.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (Grant No. 22171290, 52161135110) and the Natural Science Foundation of Guangdong Province (2022A1515011376). The vacuum ultraviolet (VUV) and far-infrared (IR) reflection spectral measurements of the samples were carried out with the support of the 4B8 beamline at the Beijing Synchrotron Radiation Facility (BSRF, Beijing, China) and the BL01B beamline at the National Synchrotron Radiation Laboratory (NSRL, Hefei, China), respectively.

## References

- P. Dorenbos, Fundamental limitations in the performance of  $\text{Ce}^{3+}$ ,  $\text{Pr}^{3+}$ , and  $\text{Eu}^{2+}$ -activated scintillators, *IEEE Trans. Nucl. Sci.*, 2010, **57**, 1162–1167.
- C. R. Ronda, *Luminescence: from theory to applications*, Wiley, Weinheim, 2007.
- W. Lü, J. S. Huo, Y. Feng, S. Zhao and H. P. You, Photoluminescence, energy transfer and tunable color of  $\text{Ce}^{3+}$ ,  $\text{Tb}^{3+}$  and  $\text{Eu}^{2+}$  activated oxynitride phosphors with high brightness, *Dalton Trans.*, 2016, **45**, 9676–9683.
- C. Li, H. W. Zheng, H. W. Wei, S. J. Qiu, L. Xu, X. M. Wang and H. Jiao, A color tunable and white light emitting  $\text{Ca}_2\text{Si}_5\text{N}_8:\text{Ce}^{3+}$ ,  $\text{Eu}^{2+}$  phosphor via efficient energy transfer for near-UV white LEDs, *Dalton Trans.*, 2018, **47**, 6860–6867.
- F. Su, B. B. Lou, Y. Y. Ou, Y. L. Yang, W. J. Zhou, C. K. Duan and H. B. Liang, VUV–UV–vis luminescence, energy transfer dynamics, and potential applications of  $\text{Ce}^{3+}$ - and  $\text{Eu}^{2+}$ -doped  $\text{CaMgSi}_2\text{O}_6$ , *J. Phys. Chem. C*, 2021, **125**, 5957–5967.
- J. Y. Ding, Q. X. Xu, J. Z. He, W. B. Zhang, J. C. Zhou and Q. S. Wu, Full spectrum light-emitting diodes based on a new efficient zirconium silicate green phosphor for healthy lighting, *Mater. Chem. Front.*, 2021, **5**, 7251–7258.
- M. Kimata, The structural properties of synthetic Sr-åkermanite,  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ , *Z. Kristallogr. – Cryst. Mater.*, 1983, **163**, 295–304.
- Z. G. Xiao and Z. Q. Xiao, Long persistence luminescent silicate material and its producing method, *CHN Pat.*, 98105078.6, 1998.
- Y. Q. Li and Y. H. Wang, Enhancement of long-persistence by  $\text{Ce}^{3+}$  co-doping in  $\text{Sr}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$ ,  $\text{Dy}^{3+}$  blue phosphor, *J. Phys.: Conf. Ser.*, 2009, **152**, 012090.
- H. Homayoni, S. Sahi, L. Ma, J. Y. Zhang, J. Mohapatra, P. Liu, A. P. Sotelo, R. T. Macaluso, T. Davis and W. Chen, X-ray excited luminescence and persistent luminescence of  $\text{Sr}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$ ,  $\text{Dy}^{3+}$  and their associations with synthesis conditions, *J. Lumin.*, 2018, **198**, 132–137.
- A. A. Coelho, *TOPAS-Academic (version 4.1)*, Coelho Software, Brisbane, Australia, 2007.
- F. Su, W. J. Zhou, Y. L. Yang, Y. Y. Ou, Z. M. Qi, C. K. Duan, M. G. Brik, P. Dorenbos and H. B. Liang, Structure, luminescence of  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  in  $\text{CaMgSi}_2\text{O}_6$  and their co-existence for the excitation-wavelength/temperature driven colour evolution, *Dalton Trans.*, 2021, **50**, 10050–10058.
- Y. L. Yang, B. B. Lou, Y. Y. Ou, F. Su, C. G. Ma, C. K. Duan, P. Dorenbos and H. B. Liang, Experimental and theoretical studies of site occupancy and luminescence of  $\text{Ce}^{3+}$  in  $\text{LiSr}_4(\text{BO}_3)_3$  for potential X-ray detecting applications, *Inorg. Chem.*, 2022, **61**, 7654–7662.
- A. A. Setlur and A. M. Srivastava, On the relationship between emission color and  $\text{Ce}^{3+}$  concentration in garnet phosphors, *Opt. Mater.*, 2007, **29**, 1647–1652.
- L. Y. Zhou, F. W. Liu, R. G. Ye, L. Lei, W. G. Guo, L. Chen, D. G. Deng and S. Q. Xu, Tunable photoluminescence and temperature sensing properties of  $\text{Ce}^{3+}$ ,  $\text{Eu}^{2+}$  co-doped  $\text{Ca}_{2-x}\text{Sr}_x\text{MgSi}_2\text{O}_7$  phosphors, *J. Lumin.*, 2021, **240**, 118417.
- P. Dorenbos, Charge transfer bands in optical materials and related defect level location, *Opt. Mater.*, 2017, **69**, 8–22.
- P. Dorenbos, The nephelauxetic effect on the electron binding energy in the  $4f^9$  ground state of lanthanides in compounds, *J. Lumin.*, 2019, **214**, 116536.
- L. Pidol, B. Viana, A. K. Harari, A. Galtayries, A. Bessière and P. Dorenbos, Optical properties and energy levels of  $\text{Ce}^{3+}$  in lutetium pyrosilicate scintillator crystal, *J. Appl. Phys.*, 2004, **95**, 7731–7737.
- P. Dorenbos, L. Pierron, L. Dinca, C. W. E. van Eijk, A. Kahn-Harari and B. Viana, 4f–5d spectroscopy of  $\text{Ce}^{3+}$  in  $\text{CaBPO}_5$ ,  $\text{LiCaPO}_4$  and  $\text{Li}_2\text{CaSiO}_4$ , *J. Phys.: Condens. Matter*, 2003, **15**, 511–520.
- Y. Y. Ou, W. J. Zhou, C. M. Liu, L. T. Lin, M. G. Brik, P. Dorenbos, Y. Tao and H. B. Liang, Vacuum referred binding energy scheme, electron–vibrational interaction, and energy transfer dynamics in  $\text{BaMg}_2\text{Si}_2\text{O}_7:\text{Ln}$  ( $\text{Ce}^{3+}$ ,  $\text{Eu}^{2+}$ ) phosphors, *J. Phys. Chem. C*, 2018, **122**, 2959–2967.
- M. Nazarov, B. Tsukerblat and D. Y. Noh, Vibronic coupling parameters and Stokes shift in thiogallate phosphors, *J. Phys. Chem. Solids*, 2008, **69**, 2605–2612.
- P. Makreski, G. Jovanovski, B. Kaitner, A. Gajović and T. Biljan, Minerals from Macedonia XVIII. Vibrational spectra of some sorosilicates, *Vib. Spectrosc.*, 2007, **44**, 162–170.
- L. T. Lin, R. Shi, R. F. Zhou, Q. Peng, C. M. Liu, Y. Tao, Y. Huang, P. Dorenbos and H. B. Liang, The effect of  $\text{Sr}^{2+}$  on luminescence of  $\text{Ce}^{3+}$ -doped  $(\text{Ca},\text{Sr})_2\text{Al}_2\text{SiO}_7$ , *Inorg. Chem.*, 2017, **56**, 12476–12484.
- Q. Peng, C. M. Liu, D. J. Hou, W. J. Zhou, C. G. Ma, G. K. Liu, M. G. Brik, Y. Tao and H. B. Liang, Luminescence of  $\text{Ce}^{3+}$ -doped  $\text{MB}_2\text{Si}_2\text{O}_8$  (M = Sr, Ba): a

- deeper insight into the effects of electronic structure and Stokes shift, *J. Phys. Chem. C*, 2016, **120**, 569–580.
- 25 J. Yan, C. M. Liu, J. Vlieland, J. B. Zhou, P. Dorenbos, Y. Huang, Y. Tao and H. B. Liang, Intense emission of  $\text{Ba}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$  under X-ray excitation for potential detecting applications, *J. Lumin.*, 2017, **183**, 97–101.
- 26 J. Yan, L. X. Ning, Y. C. Huang, C. M. Liu, D. J. Hou, B. B. Zhang, Y. Huang, Y. Tao and H. B. Liang, Luminescence and electronic properties of  $\text{Ba}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$ : a combined experimental and hybrid density functional theory study, *J. Mater. Chem. C*, 2014, **2**, 8328–8332.
- 27 J. Hölsäa, T. Laamanena, M. Lastusaaria and P. Novák, Isolated defects in  $\text{Sr}_2\text{MgSi}_2\text{O}_7$ : a DFT study, *Phys. Procedia*, 2012, **29**, 76–85.
- 28 C. K. Duan and M. F. Reid, Local field effects on the radiative lifetimes of  $\text{Ce}^{3+}$  in different hosts, *Curr. Appl. Phys.*, 2006, **6**, 348–350.
- 29 I. Petousis, D. Mrdjenovich, E. Ballouz, M. Liu, D. Winston, W. Chen, T. Graf, T. D. Schladt, K. A. Persson and F. B. Prinz, Data descriptor: High-throughput screening of inorganic compounds for the discovery of novel dielectric and optical materials, *Sci. Data*, 2017, **4**, 160134.
- 30 P. Dorenbos, Relation between  $\text{Eu}^{2+}$  and  $\text{Ce}^{3+}$  f  $\leftrightarrow$  d-transition energies in inorganic compounds, *J. Phys.: Condens. Matter*, 2003, **15**, 4797–4807.
- 31 A. A. Setlur, A. M. Srivastava, L. Pham, M. Hannah and U. Happek, Charge creation, trapping, and long phosphorescence in  $\text{Sr}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$ ,  $\text{RE}^{3+}$ , *J. Appl. Phys.*, 2008, **103**, 053513.
- 32 M. D. Birowosuto, P. Dorenbos, C. W. E. van Eijk, K. W. Kramer and H. U. Güdel, Thermal quenching of  $\text{Ce}^{3+}$  emission in  $\text{PrX}_3$  (X = Cl, Br) by intervalence charge transfer, *J. Phys.: Condens. Matter*, 2007, **19**, 256209.
- 33 Y. C. Lin, M. Bettinelli and M. Karlsson, Unraveling the mechanisms of thermal quenching of luminescence in  $\text{Ce}^{3+}$ -doped garnet phosphors, *Chem. Mater.*, 2019, **31**, 3851–3862.
- 34 Y. C. Jia, A. Miglio, S. Poncé, M. Mikami and X. Gonze, First-principles study of the luminescence of  $\text{Eu}^{2+}$ -doped phosphors, *Phys. Rev. B*, 2017, **96**, 125132.
- 35 P. Dorenbos, Mechanism of persistent luminescence in  $\text{Sr}_2\text{MgSi}_2\text{O}_7:\text{Eu}^{2+}$ ;  $\text{Dy}^{3+}$ , *Phys. Status Solidi B*, 2005, **242**, R7–R9.
- 36 M. Inokuti and F. Hirayama, Influence of energy transfer by the exchange mechanism on donor luminescence, *J. Chem. Phys.*, 1965, **43**, 1978–1989.
- 37 I. R. Martin, V. D. Rodríguez, U. R. Rodríguez-Mendoza and V. Lavin, Energy transfer with migration. Generalization of the Yokota–Tanimoto model for any kind of multipole interaction, *J. Chem. Phys.*, 1999, **111**, 1191–1194.
- 38 A. I. Burshtein, The influence of the migration mechanism of approaching particles on the energy transfer between them, *J. Lumin.*, 1980, **21**, 317–321.