

## Application of column buckling theory to steel aluminium foam sandwich panels

Vidwans, Aditya; Trovalusci, Patrizia; Fantuzzi, Nicholas; Correia, José A.F.O.

**DOI**

[10.1016/j.istruc.2023.04.112](https://doi.org/10.1016/j.istruc.2023.04.112)

**Publication date**

2023

**Document Version**

Final published version

**Published in**

Structures

**Citation (APA)**

Vidwans, A., Trovalusci, P., Fantuzzi, N., & Correia, J. A. F. O. (2023). Application of column buckling theory to steel aluminium foam sandwich panels. *Structures*, 54, 607-617.  
<https://doi.org/10.1016/j.istruc.2023.04.112>

**Important note**


To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.



# Application of column buckling theory to steel aluminium foam sandwich panels

Aditya Vidwans<sup>a,c</sup>, Patrizia Trovalusci<sup>a</sup>, Nicholas Fantuzzi<sup>b,\*</sup>, José A.F.O. Correia<sup>c,d</sup>

<sup>a</sup> Sapienza University of Rome, Department of Structural and Geotechnical Engineering, Via Gramsci 53 - 00197 Roma, Italy

<sup>b</sup> University of Bologna, Department of Civil, Chemical, Environmental and Materials Engineering, Viale del Risorgimento, 2 - 40136 Bologna, Italy

<sup>c</sup> Delft University of Technology, Faculty of Civil Engineering and Geosciences, Building 23, Stevinweg 1, 2628 CN Delft, Netherlands

<sup>d</sup> University of Porto, INEGI & CONSTRUCT, Faculty of Engineering, Rua Dr. Roberto Frias, s/n 4200-465 Porto, Portugal

## ARTICLE INFO

### Keywords:

Aluminium foam  
Sandwich  
Buckling

## ABSTRACT

In steel structures, a lot of attention is paid to lightweight structures, i.e. reduction of dead load without compromising structural safety, integrity and performance. Thanks to modern steel aluminium foam sandwich panel manufacturing technology a new possibility became available for lightweight structural design. Assessment and understanding of the behaviour of this sandwich panel under in-plane compression or flexure is crucial before its application in steel structures. Column buckling theory is considered and applied to the steel aluminium foam sandwich panel to evaluate its behaviour under in-plane compressive load. In this work, various assumptions are made to generalise Euler's buckling formula. The generalisation requires modification of the buckling stiffness expression to account for sandwich panel composite properties. The modified analytical expression is verified with finite element simulation employing various material models specific to steel faceplates and aluminium foam as well as various geometric imperfections. Based on this study, it can be concluded that Euler's buckling formula can be successfully modified and used in the prediction of the load-carrying capacity of a sandwich panel.

## 1. Introduction

Bert, Noor and Burton state that the concept behind sandwich construction can be traced back to Fairbairn in England in 1849 [1]. The first application of sandwich technology was in mosquito aircraft in England, which was used in the Second World War [2]. In the mosquito aircraft model, the sandwich construction with plywood was used. In 1969, the first successful landing of a spaceship on the moon took place [3] due to the application of various technologies such as rocket, aerospace, computer science and last but not least sandwich construction.

The most simple type of sandwich panel consists of two strong, stiff, thin plates or sheets of highly dense material separated by a thick layer of low-density material that can be much less strong and stiff [2]. Fig. 1 gives a general idea of a sandwich panel. A lot of sandwich construction can be made based on structural requirements by combining different core and face materials. This possibility of combining materials makes it possible to make an optimum structure of the sandwich panel for specific applications. In sandwich panels, it is possible to combine the positive properties of individual materials. This freedom makes it possible to make a sandwich panel with various favourable properties such

as high load-bearing capacity with low self-weight, capacity for rapid erection without heavy lift cranes or equipment, ease in installation and replacement or repair in case of damage and long life with a low maintenance cost. The payload can be raised, higher speeds can be reached and less fuel consumption can be obtained when using these lightweight materials [4]. Some of the other advantages of sandwich panels are the mass predictability, long-spanning capability, durability, pre-fabricability and finally yet importantly reusability. These characteristics justify the increasing demand and application of sandwich panels in various fields and industries.

The buckling issues are often treated as a two-dimensional problem. Global buckling of a composite sandwich structure only occurs if the core is sufficiently stiff enough in the through-thickness direction [7]. If not then face wrinkling might occur. Buckling and wrinkling are the most common failure modes for the sandwich panel. These failure modes are the basis for design for most sandwich panels. Carlsson and Kardomateas (2011) [8] gave various theoretical approaches for sandwich buckling and Howard Allen [2] did various research on these sandwich panels.

\* Corresponding author.

E-mail addresses: [aditya.vidwans@uniroma1.it](mailto:aditya.vidwans@uniroma1.it) (A. Vidwans), [patrizia.trovalusci@uniroma1.it](mailto:patrizia.trovalusci@uniroma1.it) (P. Trovalusci), [Nicholas.fantuzzi@unibo.it](mailto:Nicholas.fantuzzi@unibo.it) (N. Fantuzzi), [J.A.FonsecaOliveiraCorreia@tudelft.nl](mailto:J.A.FonsecaOliveiraCorreia@tudelft.nl), [jacorreia@fe.up.pt](mailto:jacorreia@fe.up.pt) (J.A.F.O. Correia).

<https://doi.org/10.1016/j.istruc.2023.04.112>

Received 29 December 2022; Received in revised form 13 March 2023; Accepted 27 April 2023

Available online 27 May 2023

2352-0124/© 2023 The Authors. Published by Elsevier Ltd on behalf of Institution of Structural Engineers. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

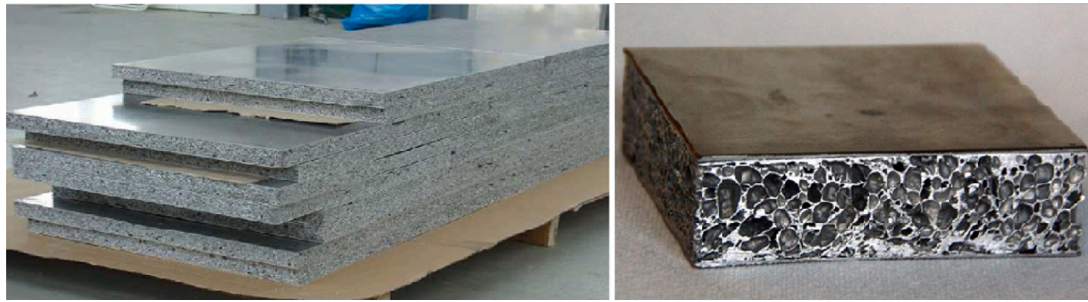


Fig. 1. Steel aluminium foam sandwich panel [5,6].

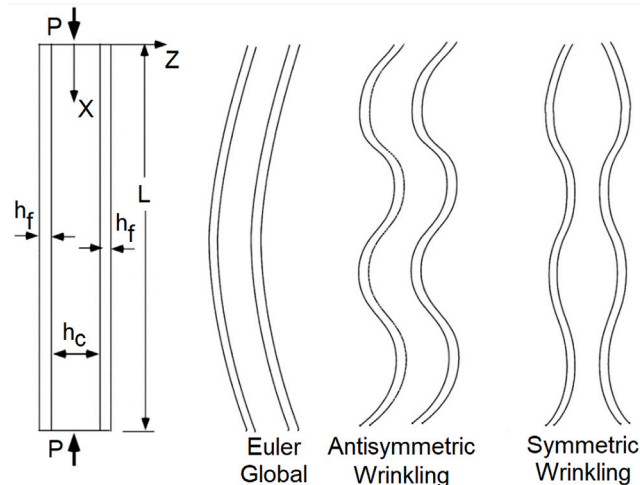


Fig. 2. Buckling modes [8].

Face wrinkling is also known as local (short wavelength) buckling. Face wrinkling will occur when the critical value of compressive stress of the face-plate is reached. Face wrinkling can be of two types: symmetric and asymmetric. In certain cases, if the load on one face is more than the other or if the thickness of the faces is unequal then the face with more load or less thickness can buckle resulting in single-sided face wrinkling. Fig. 2 gives a brief idea of sandwich panel buckling where ' $L$ ' is length, ' $P$ ' is axial compressive load, ' $h_f$ ' is thickness of face-plate and ' $h_c$ ' is thickness of core of the sandwich panel.

Various research has been done by Gough GS [9], Goodier JN [10] and Hoff NJ [11] on wrinkling problems of sandwich panels. However, as per Niu and Talreja [12], different researchers have given different results for the same wrinkling phenomenon. Some researchers did try to achieve a general method that can be applied for both the global buckling and wrinkling phenomenon. Benson and Mayers [13] were the first to suggest an approach for simultaneously solving global buckling and wrinkling questions. After the wrinkling model, Niu and Talreja [14] proposed a combined model for both wrinkling as well as global buckling. Investigations are done by Léotoing [15] on wrinkling and global buckling of sandwich panels with unified expression. In this investigation, the core material is considered as a higher-order beam model. Numerical, analytical and experimental analysis is done by Jasion [16] on wrinkling and global buckling of sandwich panels. The local buckling strength of steel foam sandwich panels has been studied by S Szyniszewski [5]. In this study, a significant strength increment is observed for a sandwich panel of steel face-plates and steel foam as compared to a solid steel plate. Recently Douville [17] used a total Lagrangian formulation for postulating an exact analytical solution for both local and global buckling of sandwich panels under various loads. All of these proposed methods and theories are pretty tedious and long to be applied in the field.

For predicting the compressive strength of the FRP sandwich panel, a new empirical design approach is presented by Martin Noël and Amir Fam [18]. A simple design model which considers both global and local failure modes and can be used for design purposes is proposed in this study. Martin Noël and Amir Fam propose an empirical model which was calibrated by using 168 test results of the concentrically loaded sandwich panel made of FFRP or GFRP face sheet and polyurethane or polyisocyanurate rigid foam cores. FRP sandwich panels are becoming popular due to their lightweight, ease and speed of installation, and high thermal insulation capabilities. Kenneth Mak, Amir Fam and Colin MacDougall [19] tried to replace conventional GFRP skins with bio-based skins made from unidirectional flax fibres and a resin blend consisting of epoxidized pine oil. In this study, a 4-point bending test is done to predict the flexural strength of the sandwich panel. A new type of composite called Layered Sandwich Beam (LSB) has been introduced by Wahid Ferdous, Allan Manalo, Thiru Aravinthan and Amir Fam [20]. Layered Sandwich Beam (LSB) is a sandwich system consisting of Phenolic cores and Glass Fibre Reinforced Polymer (GFRP) skins, and several layers of sandwich panels bonded together with an epoxy polymer matrix for manufacturing beams. In this study, shear and flexural behaviour of the LSB is investigated. In order to understand the behaviour of LSB, a numerical analysis was required and a finite element model was developed. The study demonstrates that LSB has improved sectional stability due to a reduction in wrinkling and buckling of composite skins as well as indentation failure. The study is done by Khalifa [21] to determine the quasi-static resistant function of new cost-effective lightweight cold-formed steel sandwich panels that could be used in blast-resistant structures. To predict elastic characteristics and to assess critical failure modes of this sandwich panel an analytical model is proposed. Also, eighteen sandwich panels were subjected to uniform quasi-static loads in this experimental programme. Different deck profiles were used to investigate different sandwich configurations, including longitudinal and transverse corrugated core sandwich panels. Effect of sandwich panel core configuration and core sheet thickness on sandwich panel behaviour was investigated, taking into account energy absorption and ductility. Research on the flexural behaviour of prestressed composite beams with sandwich floor panels, rather than concrete slabs is done by Ryu [22]. In this study, the sandwich plate system (SPS) was used for floor panels. This SPS consists of two steel faceplates separated by a high-density polyurethane core. The flexural performance of prestressed SPS composite beams (PSCBs) was investigated. PSCB shows excellent ductile behaviour as well as a 14% increment in the ultimate load-carrying capacity. Also, a finite element model capable of predicting the flexural behaviour of PSCB is proposed. The flexural analysis is done by Łukasz Smakosz, Ireneusz Kreja and Zbigniew Pozorski [23] on a composite structural insulated panel (CSIP) with magnesium oxide board facings and expanded polystyrene (EPS) core. A nonlinear FE model was created to stimulate the flexure behaviour of this composite. Also, lab experiments were done on this composite to verify the proposed model. A good correlation between the proposed model and the experimental result was observed.

In this paper, a simple empirical formula/analytical expression is proposed to calculate the buckling capacity of the sandwich panel.

Column buckling theory is considered and applied to the steel aluminium foam sandwich panel to evaluate its behaviour under in-plane compressive load. Various assumptions are made to generalise Euler's buckling formula. The modified analytical expression is verified with finite element simulation employing various material models specific to steel face-plates and aluminium foam as well as various geometric imperfections.

### 2. Implementation of buckling formula to sandwich panel

Euler's buckling formula was applied to calculate the buckling capacity of the sandwich panel. For the sandwich panel, some assumptions were made as follows:

- Load is applied only on face-plates, not on the core;
- Core does not contribute to the buckling capacity (load carrying capacity) of the sandwich panel;
- Core has isotropic behaviour;
- Density of the core is homogeneous;
- During the manufacturing process proper metallurgical bond is established between the core and face-plates.

These assumptions allow Eq. (1) to be used in order to calculate the sandwich panel's moment of inertia.

$$I = b(t^3 - t_c^3)/12 \tag{1}$$

The core is made from a material with a really small modulus of elasticity as compared to face-plate. Therefore, its contribution to buckling stiffness is ignored. The following procedure can be followed to calculate the buckling capacity of the sandwich panel.

Using Eq. (2), the buckling stiffness of the sandwich will be:

$$EI = E_f b(t^3 - t_c^3)/12 \tag{2}$$

As shown in Eq. (3), the Euler elastic critical buckling load can be described as:

$$N_{cr} = \pi^2 EI / L^2 \tag{3}$$

From this, the slenderness of the sandwich can be calculated as (Eq. (4)),

$$\lambda = \sqrt{Af_y / N_{cr}} \tag{4}$$

where,

$$A = 2bt_f \tag{5}$$

$$t = t_c + 2t_f \tag{6}$$

Therefore, the reduction factor is given by (Eq. (7)),

$$\chi = 1 / (\phi + \sqrt{\phi^2 - \lambda^2}) \tag{7}$$

where,

$$\phi = 0.5[1 + \alpha(\lambda - 0.2) + \lambda^2] \tag{8}$$

Therefore, as per column buckling theory, the resistance of the sandwich panel can be given by (Eq. (9)),

$$N_{bRd} = \chi Af_y \tag{9}$$

### 3. FEA model

In this study, for FEA, the same assumptions are considered as in Section 2.

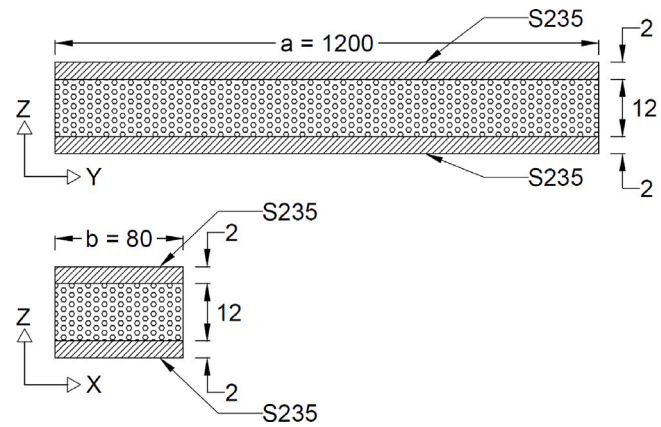


Fig. 3. Dimension of sandwich panel specimen (mm). Source: Reproduced based on ref. S.S. Metal (2018) [24].

#### 3.1. Considered model

A full-scale three-dimensional model was considered based on the dimensions as shown in Fig. 3.

In Fig. 3, 'a' is the length and 'b' is the width of the sandwich panel. The dimensions of sandwich panels are 1200 mm in length, 80 mm in width with a total thickness of 16 mm. This thickness is composed of 2 mm thick face-plates and 12 mm thick core. The face-plates are made of steel with a yield strength of 235 MPa, a modulus of elasticity of 210 GPa, a Poisson's ratio of 0.3, and a density of 7850 kg/m<sup>3</sup>. The core is made of aluminium foam with a yield strength of 5 MPa, modulus of elasticity of 500 MPa, Poisson's ratio of 0.3 and density of 700 kg/m<sup>3</sup>. The boundary conditions of the sandwich panel are illustrated in Fig. 4. The bottom edge of the sandwich panel is constrained from all degrees of freedom except for rotation around the x-axis. At the top edge rotation around the x-axis and displacement along the y-axis is free and all other degrees of freedom are constrained. There are no constraints on the side edges of the sandwich panel. These boundary conditions are applied to stimulate the column behaviour of the sandwich panel.

In Fig. 4, 'U<sub>x</sub>', 'U<sub>y</sub>', 'U<sub>z</sub>' are displacements along x, y and z directions, respectively and 'θ<sub>x</sub>', 'θ<sub>y</sub>', 'θ<sub>z</sub>' are the rotations around x, y and z directions, respectively.

The sandwich plane is loaded with in-plane compression along the y-axis and the displacement-controlled analysis is done. The displacement is applied only on face-plate since the contribution of the core to buckling is assumed negligible. The displacement that creates in-plane compression is applied in small increments. The reaction force corresponding to each increment is observed and it is possible to conclude that with an increase in the applied displacement, the corresponding force reaction increases and at a specific point the value of the force reaction drops (decreases). The force reaction corresponding to this point is considered as a load-carrying capacity of the sandwich panel. The Fig. 4 shows the applied displacement on the sandwich panel.

For modelling in ANSYS, SOLID186 element type is used. SOLID186 is a second-order 3-D 20-node solid element that exhibits quadratic displacement behaviour and it has 20 nodes having three degrees of freedom per node (x, y and z-direction). SOLID186 is an element which offers the ability to model local bending effects and because of its quadratic element property, it prevents hourglassing and shear locking. In this study, three elements are used in the through-thickness direction to prevent hour-glassing [25].

To verify the modified analytical expression, a finite element simulation employing various material models specific to steel face-plates and aluminium foam as well as various geometric imperfections was done.

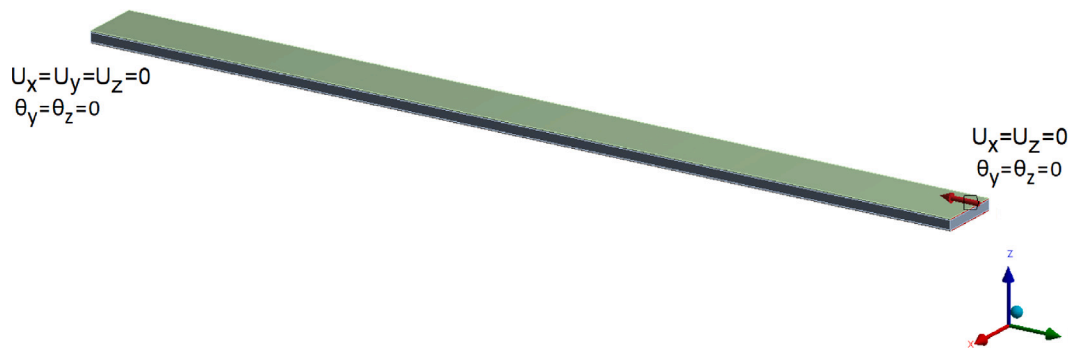


Fig. 4. Loading and boundary conditions of sandwich panel.

Table 1

Design values of global geometric imperfection [27].

Model	Imperfection	Value of Imperfection(Global)
a	L/300	4
b	L/250	4.8
c	L/200	6
d	L/150	8

\* L represents the length of the member.

Table 2

Design value of local geometric imperfection [27].

Type	Imperfection	Value of Imperfection
Local	Min(a/200,b/200)	0.4

\* a represents the length of the member.

\* b represents the width of the member.

### 3.2. Material models

The mechanical properties of the material can be illustrated with the help of stress–strain curves. In this study, the bi-linear model of steel, the multi-linear model of steel and the bi-linear model of aluminium foam are considered. Eurocode 1993-1-5 [26] gives four different material models for the FE model. For the finite element analysis, the true stress–strain curve and bi-linear material model used for steel are illustrated in Fig. 5(a) and Fig. 5(b). In the case of aluminium foam, only a few material properties are known. Therefore, only the bi-linear material model of foam with no strain hardening is considered. The material model used for aluminium is shown in Fig. 6.

### 3.3. Geometric imperfections

Geometric imperfections can be global and local. The adopted non-linearity analysis approach incorporates both imperfections, curved geometry of panel in the global sense as well as imperfections on the local level. When the imperfection effect exists, the total stress is a result of stress due to axial load and bending. The strength of the steel member is always sensitive to imperfection in the shape of its Eigen-modes. Buckling modes of the structure taken from an Eigen buckling analysis can be used as elementary imperfection shapes. In ANSYS, initial deformation shapes can be easily imposed in the shape of Eigen buckling modes with a user-defined magnitude.

In this case, four different models with different values of imperfections are considered. Table 1 shows different values of the imperfections imposed on the structure. Fig. 7 represents an idea of the structure with an imposed global geometric imperfection.

Along with global imperfection, local imperfections can also exist in the structure. Table 2 shows the values of imperfection imposed on the structure.

Fig. 8 displays structure with local geometric imperfection,

## 4. FEA analysis

A finite element analysis considering geometric imperfections and material non-linearity (models) is used to determine the resistance of sandwich panel under pure compression. Eigen buckling analysis is done to get critical buckling load and buckling shapes. These buckling shapes will be used as initial imperfections in nonlinear analysis and the first fifty buckling shapes/modes are evaluated and plotted in the analysis.

As it is stated before that, imperfections in the shape of buckling modes are critical. Mode 1 is the first Eigen buckling mode, which results in the global buckling of sandwich panel with 1 half sine. Mode 42 shows the global buckling of sandwich panel with 42 half-sines. Until mode 43, sandwich panel was showing global buckling with the respective number of half sines. However, at mode 43 instead of buckling in 43 half sines sandwich started buckling on a local scale i.e., local buckling of face-plates is observed. Therefore, mode 43 is the first mode, which gives local buckling or local imperfections in a sandwich panel and these local imperfections observed in the face-plate are continuous or uniform. Thus, mode 1 is the first critical buckling mode which gives global buckling whereas mode 43 is the first critical buckling mode which gives local buckling and for that reason 1st buckling mode and 43rd buckling mode were used to impose global and local imperfections, respectively.


### 4.1. Global geometric imperfection

Buckling analysis is done on a sandwich with global geometric imperfection and various material models. These models are:


- Global geometric imperfections;
- Global geometric imperfections with steel bi-linear & aluminium linear;
- Global geometric imperfections with steel bi-linear & aluminium bi-linear;
- Global geometric imperfections with steel multi-linear & aluminium linear;
- Global geometric imperfections with steel multi-linear & aluminium bi-linear;

Table 3 shows the loads that can be applied when global geometric imperfections are considered along with various material models. The load values were calculated with the help of finite element analysis.

To find the resistance of the sandwich panel a non-linear analysis of the sandwich panel is performed. In this non-linear analysis, an applied displacement and its resultant force was calculated. The displacement was applied in short increments until the point where it is not possible to achieve force convergence and the model fails. The displacement increment and force reaction corresponding to it is arranged in a tabular form. The maximum force reaction can be treated as the load-carrying capacity of the sandwich panel. In addition, to visualise this,

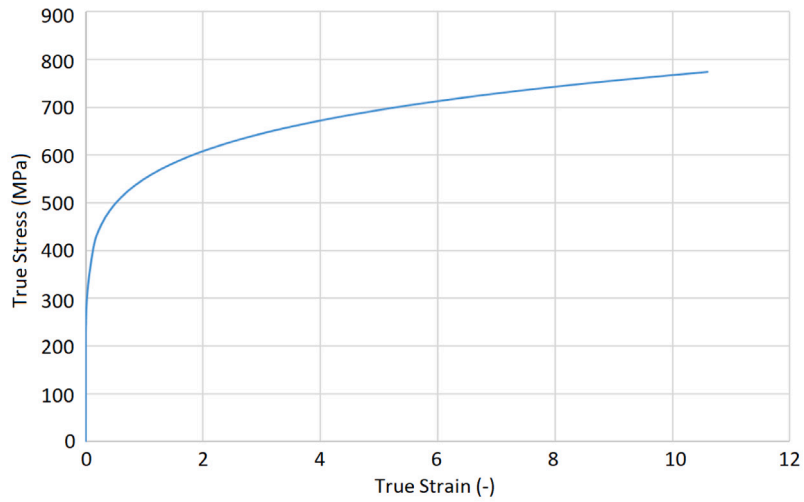

(a) Steel material model multi-linear

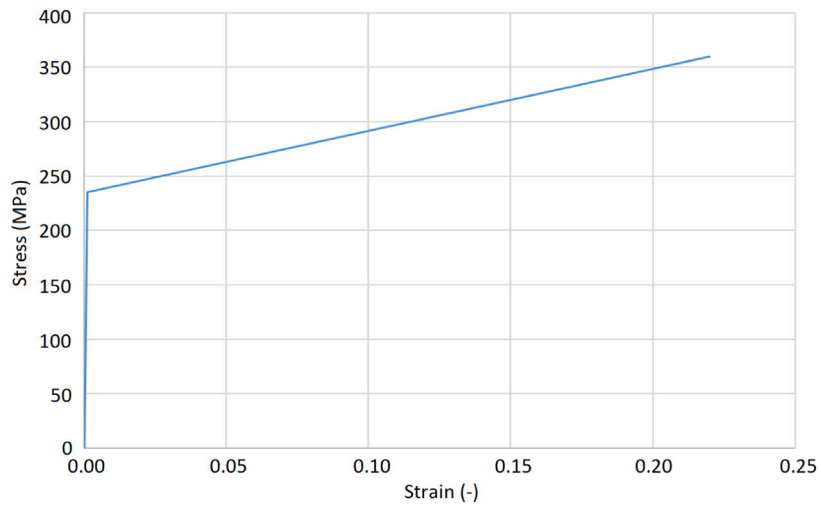

(b) Steel material model bi-linear

Fig. 5. Steel material models.

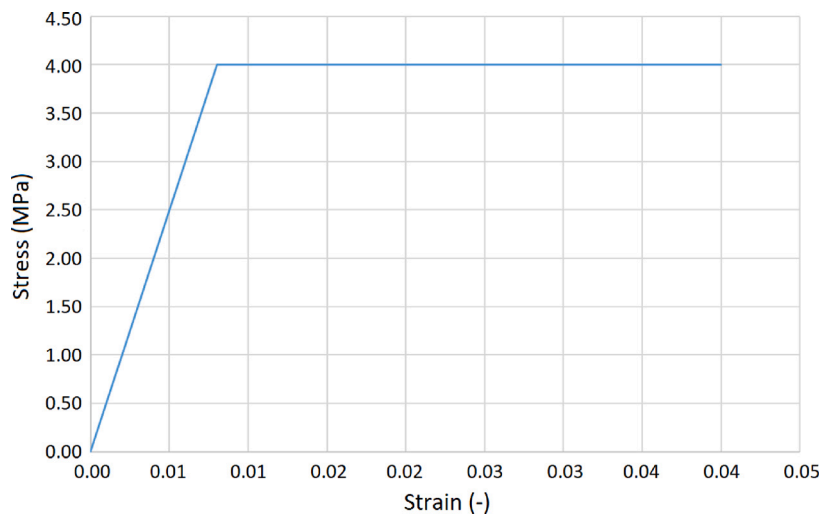


Fig. 6. Aluminium material model bi-linear.

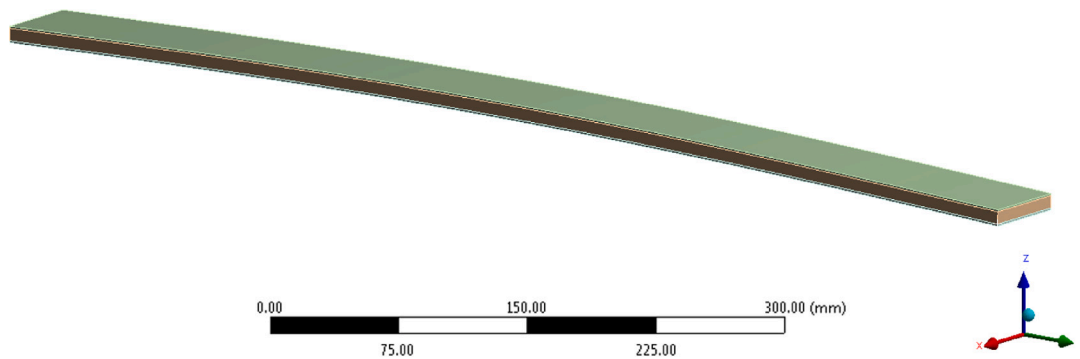


Fig. 7. Global geometric imperfection.

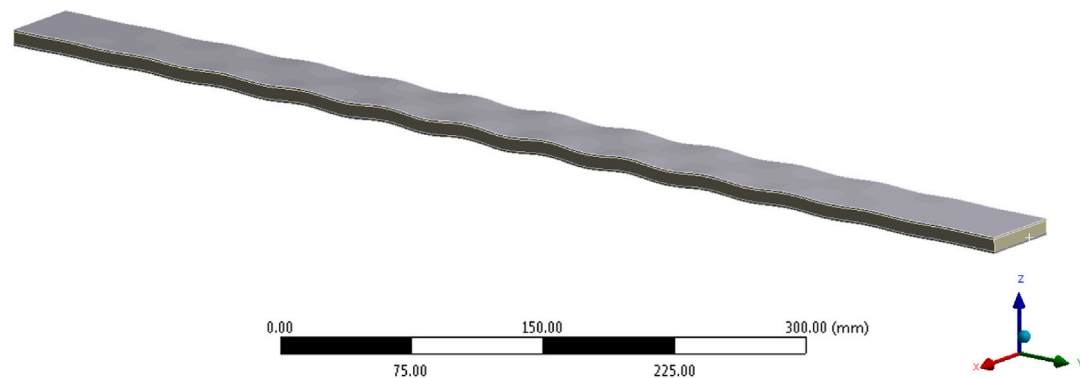


Fig. 8. Local geometric imperfection.

**Table 3**  
Result of FE Analysis on a sandwich with global geometric imperfection and material models.

Load corresponding to first Eigen buckling mode (kN)	Geometric imperfection model	Load (kN)			
		Various material models			
		Steel Bi-Linear and Aluminium Linear	Steel Bi-Linear and Aluminium Bi-Linear	Steel Multi-Linear and Aluminium Linear	Steel Multi-Linear and Aluminium Bi-Linear
20.9	a	9.8	9.8	10	10
	b	9.5	9.5	9.8	9.8
	c	9.3	9.3	9.6	9.6
	d	8.9	8.9	9.2	9.2

the graph between displacement increment and corresponding force reaction is plotted as shown in Fig. 10 and Fig. 11. Fig. 9 shows in-plane and out-of-plane displacement of the sandwich panel. (see Figs. 9 and 13–15). ,

#### 4.2. Local geometric imperfection

Buckling analysis is done on a sandwich with local geometric imperfection and various material models. These models are:

- Local geometric imperfections;
- Local geometric imperfections with steel bi-linear & aluminium linear;
- Local geometric imperfections with steel bi-linear & aluminium bi-linear;
- Local geometric imperfections with steel multi-linear & aluminium linear;
- Local geometric imperfections with steel multi-linear & aluminium bi-linear;

Table 4 shows the loads that can be applied when local geometric imperfections are considered along with various material models. The load values were calculated with the help of finite element analysis.

In addition, to visualise this, the graph between displacement increment and corresponding force reaction can be plotted as shown in Fig. 12.

#### 4.3. Combined local & global imperfection

In the above cases, global and local imperfections are considered separately but in practice, global and local imperfections can occur simultaneously in structure. This might result in an additional reduction in the load-carrying capacity of the structure. This value of load can be calculated analytically with Eq. (10),

$$F/F_{buck,global} + F/F_{buck,local} \leq 1 \tag{10}$$

According to Eq. (10), the load-carrying capacity of a sandwich panel with both local and global imperfections is calculated and arranged in Table 5:

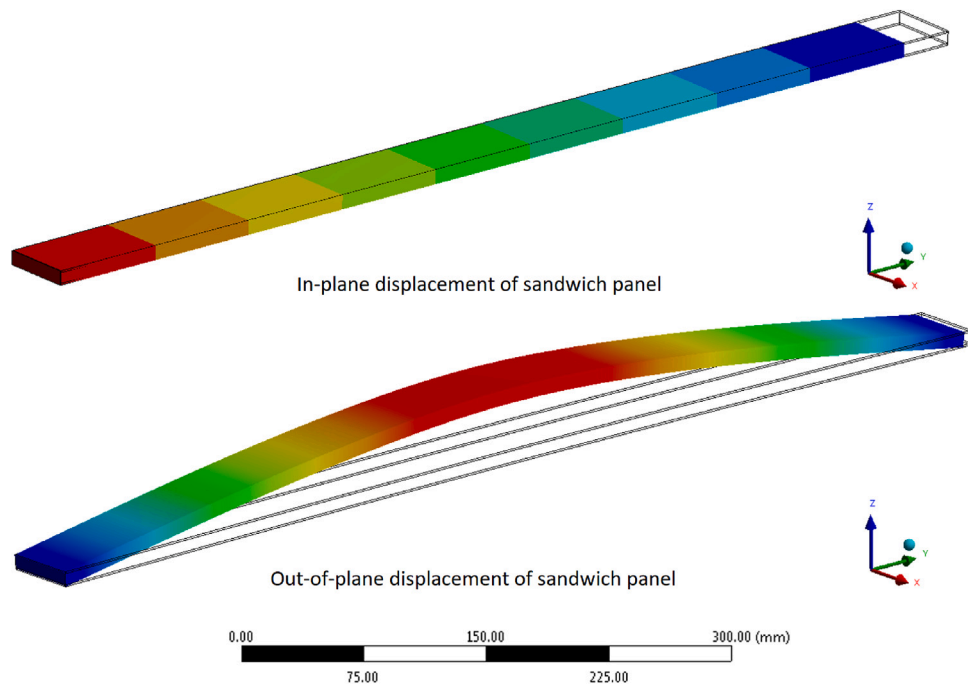


Fig. 9. Displacement of sandwich panel.

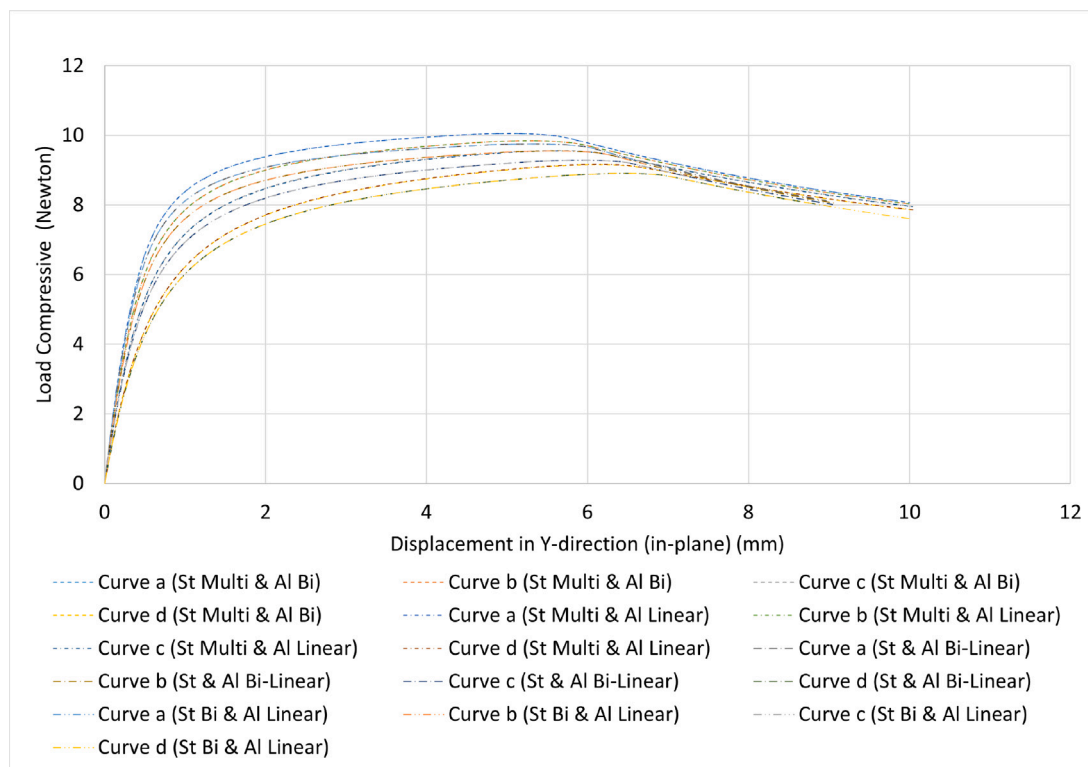


Fig. 10. Graph between in-plane displacement vs compressive load (global imperfection).

## 5. Comparison of buckling loads

A reduction factor can be used to compare the value of Eigen buckling load with load at buckling calculated with help of FEA. The reduction factor will illustrate a reduction in Eigen buckling load due to the presence of various geometric imperfections and considered material models.

### 5.1. Global imperfections

The values from Table 6 are arranged and illustrated in Fig. 13. From Table 6, it can be observed that in the case of the global imperfection, the material model used for face-plates affects the buckling capacity of the sandwich panel. On the other hand, the material model used for the core has a negligible impact on the buckling capacity of



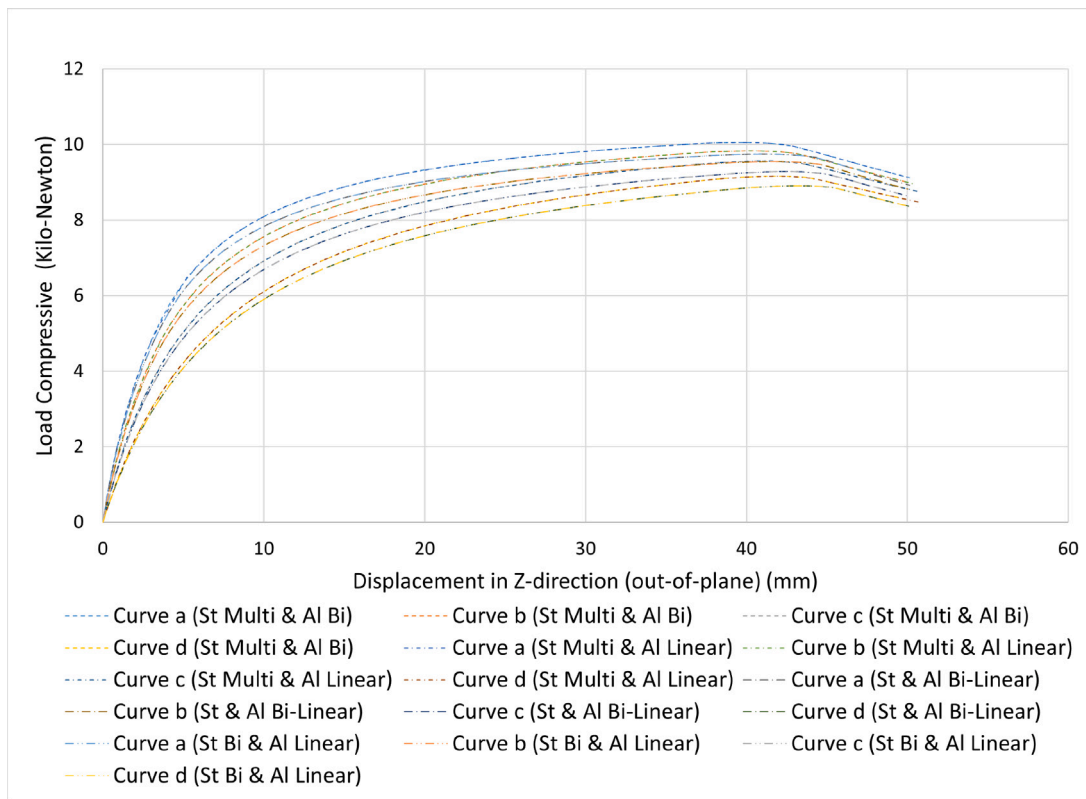


Fig. 11. Graph between out-of-plane displacement vs compressive load (global imperfection).

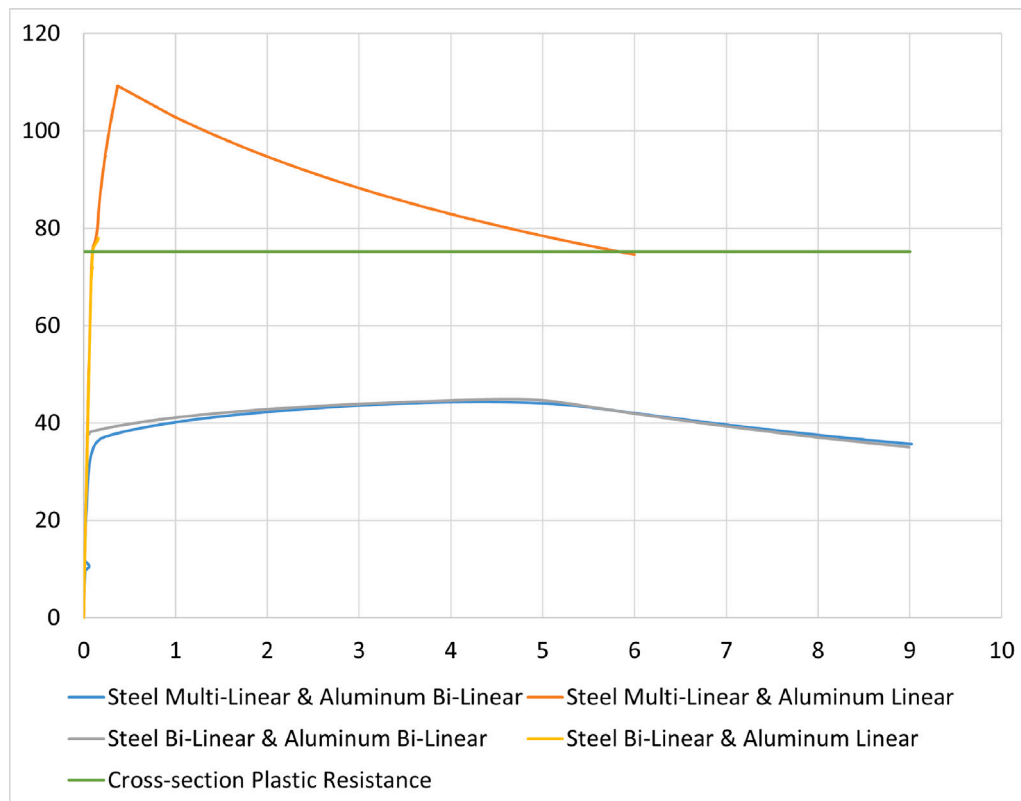


Fig. 12. Graph between out-of-plane displacement vs compressive load (local imperfection).

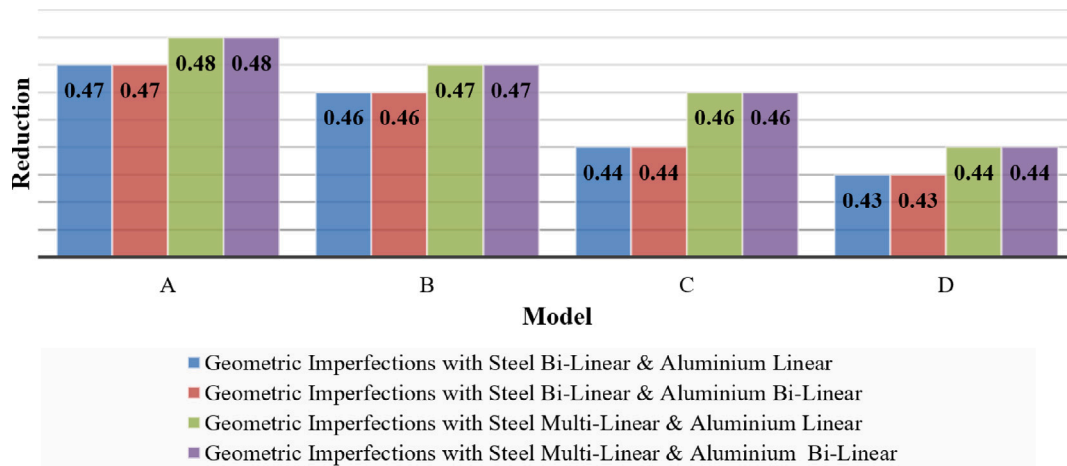


Fig. 13. Graphical representation of reduction in buckling load for considered global geometric imperfection and material models.

**Table 4**  
Result of FE Analysis on a sandwich with local geometric imperfection and material models.

Load (kN)			
Local Geometric Imperfections with Steel Bi-Linear and Aluminium Linear	Local Geometric Imperfections with Steel Bi-Linear and Aluminium Bi-Linear	Local Geometric Imperfections with Steel Multi-Linear and Aluminium Linear	Local Geometric Imperfections with Steel Multi-Linear and Aluminium Bi-Linear
80	45	109	44

**Table 5**  
Result of FE Analysis on a sandwich with global and local geometric imperfection and material models.

Load corresponding to first Eigen buckling mode (kN)	Geometric imperfection model	Load (kN)			
		Various material models			
		Steel Bi-Linear and Aluminium Linear	Steel Bi-Linear and Aluminium Bi-Linear	Steel Multi-Linear and Aluminium Linear	Steel Multi-Linear and Aluminium Bi-Linear
20.9	a	8.7	8.0	9.2	8.2
	b	8.5	7.9	9.0	8.1
	c	8.3	7.7	8.8	7.9
	d	8.0	7.4	8.5	7.6

**Table 6**  
Reduction in buckling load for considered global geometric imperfection and material models.

Geometric imperfection model	Reduction in Buckling Load			
	Various material models			
	Steel Bi-Linear and Aluminium Linear	Steel Bi-Linear and Aluminium Bi-Linear	Steel Multi-Linear and Aluminium Linear	Steel Multi-Linear and Aluminium Bi-Linear
a	0.47	0.47	0.48	0.48
b	0.46	0.46	0.47	0.47
c	0.44	0.44	0.46	0.46
d	0.43	0.43	0.44	0.44

**Table 7**  
Reduction in buckling load for considered global and local geometric imperfection and material models.

Geometric Imperfection Model	Reduction in Buckling Load			
	Various material models			
	Steel Bi-Linear and Aluminium Linear	Steel Bi-Linear and Aluminium Bi-Linear	Steel Multi-Linear and Aluminium Linear	Steel Multi-Linear and Aluminium Bi-Linear
a	0.41	0.38	0.44	0.39
b	0.41	0.38	0.43	0.39
c	0.40	0.37	0.42	0.38
d	0.38	0.36	0.40	0.36

the sandwich panel. This might be due to the fact that on a global scale contribution of the core to the buckling capacity of the sandwich panel is negligible. This also validates the assumption, made for calculating the buckling capacity of a sandwich panel, that the core does not contribute to the buckling strength of the sandwich panel.

5.2. Combined local & global imperfection

The values from Table 7 are arranged and illustrated in Fig. 14. From Table 7, it can be observed that in the case of combined global and local imperfection, the material model used for face-plates and core affects the buckling strength of the sandwich panel. This can be

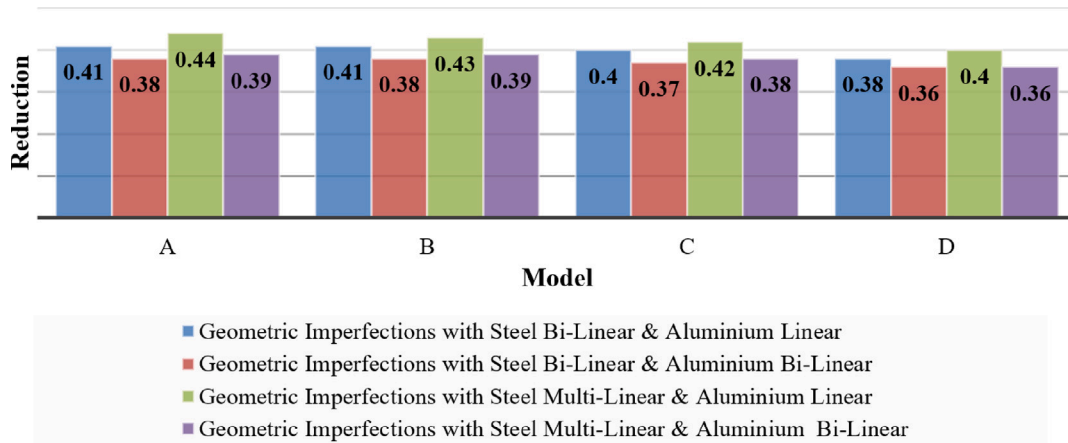


Fig. 14. Graphical representation of reduction in buckling load for considered global and local geometric imperfection and material models.

explained with help of the formula proposed by Howard Allen [2]. According to this, the critical stress for face wrinkling is largely dependent on the modulus of elasticity of the core. The formula proposed by Howard Allen [2] is as follows,

$$\sigma_{cr} = B_1 E_f^{1/3} E_c^{2/3} \tag{11}$$

Where, B1 is a constant base on Poisson’s ratio of the core.

6. Conclusion

This study is focused on the generalisation and modification of Euler’s buckling formula, such that it can be applied to sandwich beams. It also focuses on the verification of this formula with the help of finite element analysis. Based on this study, it can be concluded that Euler’s buckling formula can be successfully modified and used in the prediction of the load-carrying capacity of a sandwich panel.

In presence of geometric imperfections, material models used for face-plates have a significant impact on load-carrying capacity, whereas material models of core have a very small or negligible impact on the load-carrying capacity of a sandwich panel. This is because, on a global scale, the core has no contribution to the buckling resistance of the sandwich panel. This also justifies the theory, which states that the contribution of the core to buckling stiffness is negligible. As per the theory, the stiffness of the sandwich panel can be calculated using Eq. (12),

$$EI = E_f b(t^3 - t_c^3)/12 \tag{12}$$

From this equation, it can be observed that the stiffness of the panel is dependent on the modulus of elasticity of the face-plate. This can explain why the material model used for face-plate has a considerable impact on the load-carrying capacity of a sandwich panel with global imperfection.

In the presence of local imperfections, material models used for both face-plate and core greatly affect the load-carrying capacity of a sandwich panel. As per Howard Allen [2], stress for face wrinkling can be calculated by Eq. (13),

$$\sigma_{cr} = B_1 E_f^{1/3} E_c^{2/3} \tag{13}$$

Where, B1 is a constant base on the poison’s ratio of the core. The stress acting between the face-plate and the supporting elastic medium, which is the core, is depicted in Fig. 15.

From this equation, it can be observed that critical stress is largely dependent on the modulus of elasticity of the core. This can explain why the material model used for the core has a considerable impact on the load-carrying capacity of a sandwich panel with local imperfection.

It is encouraged to continue an investigation for sandwich panels in steel constructions to keep on pushing limitations. The lab test should

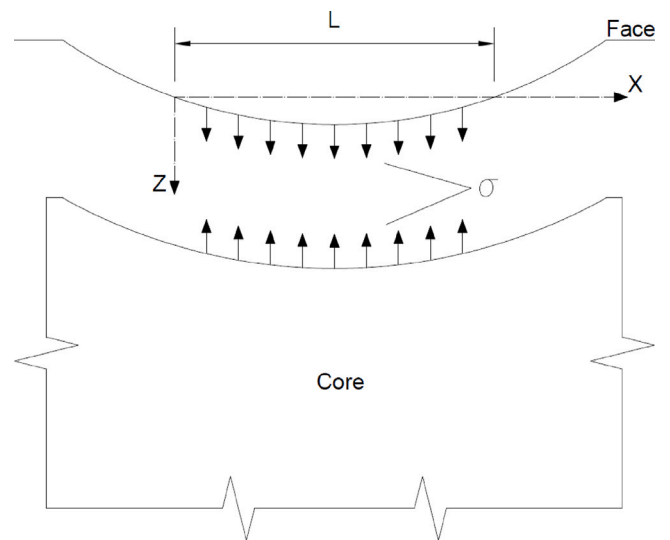


Fig. 15. Stress between the face-plate and supporting elastic medium (core)[2].

be done on the sandwich panel so as to justify this proposed theory. Also, compression and buckling tests should be done on a sandwich panel and numerical and experimental data should be compared. This will also help in understanding the real-life behaviour of sandwich panels under in-plane compression and flexural buckling. More research should be done to establish some rule like the Eurocode, which can be referred to during designing a structure with sandwich panels.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

This study was supported by the Delft University of Technology and Huisman Equipment. Also, thanks to Ben van de Geer, Alexander Richter & Havel Metal Foams for providing all the information related to the sandwich panel which was required for this study as well as giving me an opportunity to visit their production facility which was an enriching experience.

## Appendix. Notation

The following symbols are used in this paper:

$A$	= Total area of both face-plates of the sandwich panel ( $\text{mm}^2$ );
$B_1$	= Constant based on Poisson's ratio of core;
$b$	= Width of the sandwich panel (mm);
$EI$	= Buckling stiffness of the sandwich panel ( $\text{N} - \text{mm}^2$ );
$E_c$	= Modulus of elasticity of the core of the sandwich panel (MPa);
$E_f$	= Modulus of elasticity of the face-plate of the sandwich panel (MPa);
$F$	= Load-carrying capacity of a sandwich with both local & global imperfections (kN);
$F_{\text{buck,global}}$	= Load-carrying capacity of a sandwich panel with global imperfections (kN);
$F_{\text{buck,local}}$	= Load-carrying capacity of a sandwich panel with local imperfections (kN);
$f_y$	= Yield strength of face-plates of the sandwich panel (MPa);
$I$	= Moment of inertia of the sandwich panel ( $\text{mm}^4$ );
$L$	= Length of the sandwich panel (mm);
$N_{\text{fRd}}$	= Buckling resistance of the sandwich panel (MPa);
$N_{\text{cr}}$	= Euler elastic critical buckling load of the sandwich panel (N);
$t$	= Total thickness of the sandwich panel (mm);
$t_c$	= Thickness of core of the sandwich panel (mm);
$t_f$	= Thickness of face-plate of the sandwich panel (mm);
$U_x$	= Displacement along x direction (mm);
$U_y$	= Displacement along y direction (mm);
$U_z$	= Displacement along z direction (mm);
$\theta_x$	= Rotation along x direction;
$\theta_y$	= Rotation along y direction;
$\theta_z$	= Rotation along z direction;
$\sigma_{\text{cr}}$	= Critical stress for face wrinkling of the sandwich panel (MPa);
$\alpha$	= Imperfection factor;
$\lambda$	= Non-dimensional slenderness of the sandwich panel;
$\phi$	= Constant to determine the reduction factor $\chi$ ; and
$\chi$	= Reduction factor.

## References

- [1] Vinson JR. Sandwich structures: past, present, and future. In: Sandwich structures 7: Advancing with sandwich structures and materials. Springer; 2005, p. 3–12.
- [2] Allen HG. Analysis and design of structural sandwich panels: the commonwealth and international library: structures and solid body mechanics division. Elsevier; 2013.
- [3] Herrmann AS, Zahlen PC, Zuardy I. Sandwich structures technology in commercial aviation. In: Sandwich structures 7: Advancing with sandwich structures and materials. Springer; 2005, p. 13–26.
- [4] Crupi V, Epasto G, Guglielmino E. Impact response of aluminum foam sandwiches for light-weight ship structures. Metals 2011;1(1):98–112.
- [5] Szyniszewski S, Smith B, Hajjar J, Arwade S, Schafer B. Local buckling strength of steel foam sandwich panels. Thin-Walled Struct 2012;59:11–9.
- [6] Foam HM. Innovative lightweight constructions of aluminium foam. Havel Metal Foam, Brochure 2016;1–19.
- [7] Daniel I, Gdoutos E, Wang K-A, Abot J. Failure modes of composite sandwich beams. Int J Damage Mech 2002;11(4):309–34, Cited by: 160; All Open Access, Green Open Access.
- [8] Carlsson LA, Kardomateas GA. Structural and failure mechanics of sandwich composites, Vol. 121. Springer Science & Business Media; 2011.
- [9] Gough G, Elam C, Tipper G, De Bruyne N. The stabilisation of a thin sheet by a continuous supporting medium. Aeronaut J 1940;44(349):12–43.
- [10] Goodier J, Neou I. The evaluation of theoretical critical compression in sandwich plates. J Aeronaut Sci 1951;18(10):649–56.
- [11] Hoff NJ, Mautner S. The buckling of sandwich-type panels. J Aeronaut Sci 1945;12(3):285–97.
- [12] Niu K, Talreja R. Modeling of wrinkling in sandwich panels under compression. J Eng Mech 1999;125(8):875–83.
- [13] Benson AS, Mayers J. General instability and face wrinkling of sandwich plates-unified theory and applications. AIAA J 1967;5(4):729–39.
- [14] Niu K. Compressive behavior of sandwich panels and laminates with damage. Georgia Institute of Technology; 1998.
- [15] Léotoing L, Drapier S, Vautrin A. First applications of a novel unified model for global and local buckling of sandwich columns. Eur J Mech A Solids 2002;21(4):683–701.
- [16] Jasion P, Magnucka-Blandzi E, Szyk W, Magnucki K. Global and local buckling of sandwich circular and beam-rectangular plates with metal foam core. Thin-Walled Struct 2012;61:154–61.
- [17] Douville M-A, Le Grogne P. Exact analytical solutions for the local and global buckling of sandwich beam-columns under various loadings. Int J Solids Struct 2013;50(16–17):2597–609.
- [18] Noel M, Fam A. Empirical design equation for compression strength of lightweight FRP sandwich panel walls. J Archit Eng 2021;27(3). Cited by: 0.
- [19] Mak K, Fam A, Macdougall C. Flexural behavior of sandwich panels with bio-FRP skins made of flax fibers and epoxidized pine-oil resin. J Composites Constr 2015;19(6). Cited by: 50.
- [20] Ferdous W, Manalo A, Aravinthan T, Fam A. Flexural and shear behaviour of layered sandwich beams. Constr Build Mater 2018;173:429–42, Cited by: 47.
- [21] Khalifa YA, Tait MJ, El-Dakhkhni WW. Out-of-plane behavior of lightweight metallic sandwich panels. J Perform Constr Facilities 2017;31(5). Cited by: 3.
- [22] Ryu J, Lho S-H, Lee C-H, Ju YK. Flexural behavior of prestressed sandwich plate system composite beams. Eng Struct 2020;215. Cited by: 5.
- [23] Smakosz Ł, Kreja I, Pozorski Z. Flexural behavior of composite structural insulated panels with magnesium oxide board facings. Arch Civ Mech Eng 2020;20(4).
- [24] Havel metal foam GmbH, Germany & University of Surrey E. 2-point-bending test series comparison of the buckling behavior of steel-aluminum foam-sandwiches. Havel Metal Foam GmbH, Germany 2018.
- [25] Peter K. Ansys theory reference manual, release 5.6. Ansys Inc; 1994.
- [26] Beg D, Kuhlmann U, Davaine L, Braun B. Design of plated structures: Eurocode 3: Design of steel structures, Part 1-5: Design of plated structures. John Wiley & Sons; 2012.
- [27] Eurocode. Eurocode 3: Design of steel structures-Part 1-1: General rules and rules for buildings. Eur Comm Standardization 2005.